

IV-D-1

CENTRAL RESEARCH LIBRARY  
DOCUMENT COLLECTION

AEC RESEARCH AND DEVELOPMENT REPORT



MARTIN MARIETTA ENERGY SYSTEMS LIBRARIES



3 4456 0349644 7

ORNL 1702  
Chemistry-General

cy. 4A

DECLASSIFIED

CLASSIFICATION CHANGED TO:

BY AUTHORITY OF:

BY:


*E. J. Murphy 11-2-61*  
*D. B. Baer 11-3-62*

LABORATORY RECORD  
1964



A SUMMARY OF DENSITY MEASUREMENTS ON  
MOLTEN FLUORIDE MIXTURES AND A  
CORRELATION FOR PREDICTING DENSITIES  
OF FLUORIDE MIXTURES

S. I. Cohen  
T. N. Jones

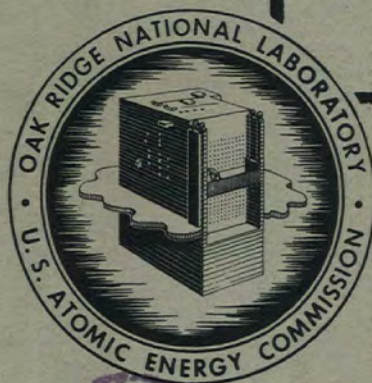

CENTRAL RESEARCH LIBRARY  
DOCUMENT COLLECTION

**LIBRARY LOAN COPY**

**DO NOT TRANSFER TO ANOTHER PERSON**

If you wish someone else to see this document,  
send in name with document and the library will  
arrange a loan.

OAK RIDGE NATIONAL LABORATORY  
OPERATED BY  
CARBIDE AND CARBON CHEMICALS COMPANY  
A DIVISION OF UNION CARBIDE AND CARBON CORPORATION



POST OFFICE BOX P  
OAK RIDGE, TENNESSEE



REPRODUCED BY THE NATIONAL ARCHIVES  
Pursuant to the provisions of the National Archives and Records Administration  
Preservation Act of 1980, the reproduction of this document in any form or by any  
means is prohibited.

ORNL-1702

This document consists of 38 pages  
Copy 4 of 222 copies Series A

Contract No W-7405-eng-26

Reactor Experimental Engineering Division

A SUMMARY OF DENSITY MEASUREMENTS ON MOLTEN FLUORIDE MIXTURES  
AND A CORRELATION FOR PREDICTING DENSITIES  
OF FLUORIDE MIXTURES

S I Cohen  
T N Jones

DATE ISSUED

JUL 19 1954

OAK RIDGE NATIONAL LABORATORY  
Operated by  
CARBIDE AND CARBON CHEMICALS COMPANY  
A Division of Union Carbide and Carbon Corporation  
Post Office Box P  
Oak Ridge, Tennessee



3 4456 0349644 7

INTERNAL DISTRIBUTION

1	C E Center	56	A D Callihan
2	Biology Library	57	G W Keilholz
3	Health Physics Library	58	J B Trice
4-5	Central Research Library	59	A P Fraas
6	Reactor Experimental	60	R W Bussard
	Engineering Library	61	M E LaVerne
7-13	Laboratory Records Department	62	E S Bettis
14	Laboratory Records, ORNL R C	63	J L Meem
15	C E Larson	64	G A Cristy
16	L B Emlet (K-25)	65	W B Cottrell
17	J P Murray (Y-12)	66	H W Savage
18	A M Weinberg	67	C P Coughlen
19	E H Taylor	68	G M Adamson
20	E D Shipley	69	L A Mann
21	C E Winters	70	G M Nessle
22	F C VonderLage	71	J O Bradfute
23	W H Jordan	72	S I Cohen
24	J A Swartout	73	N D Greene
25	S C Lind	74	D C Hamilton
26	F L Culler	75	H W Hoffman
27	A H Snell	76	F E Lynch
28	A Hollaender	77	L D Palmer
29	M T Kelley	78	W D Powers
30	W J Fretague	79	M W Rosenthal
31	G H Clewett	80	T N Jones
32	K Z Morgan	81	W D Manly
33	T A Lincoln	82	G P Smith
34	A S Householder	83	J V Cathcart
35	C S Harrill	84	M T Robinson
36	D S Billington	85	C B Mills
37	D W Cardwell	86	W R Grimes
38	E M King	87	F F Blankenship
39	R N Lyon	88	C J Barton
40	J A Lane	89	C J Barton
41	A J Miller	90	L G Overholser
42	R B Briggs	91	P A Agron
43	A S Kitzes	92	F Kertesz
44	O Sisman	93	E G Bohlmann
45	R W Stoughton	94	H C Claiborne
46	C F Graham	95	M C Edlund
47	W R Gall	96	M Tobias
48	H F Poppendiek	97	M A Bredig
49	S E Beall	98	J S Culver
50	J P Gill	99	J Y Estabrook
51	D D Cowen	100	N F Lansing
52	W M Breazeale (consultant)	101	E R Van Artsdalen
53	R A Charpie	102	J M Warde
54	W K Ergen	103	D J Sasnor
55	E P Blizzard	104	G C Williams



EXTERNAL DISTRIBUTION

105 American Cyanamid Company  
106-113 Argonne National Laboratory  
114 Armed Forces Special Weapons Project (Sandia)  
115 Army Chemical Center  
116-120 Atomic Energy Commission, Washington  
121 Battelle Memorial Institute  
122-123 Brookhaven National Laboratory  
124-125 Carbide and Carbon Chemicals Company (C-31 Plant)  
126-128 Carbide and Carbon Chemicals Company (K-25 Plant)  
129-132 Carbide and Carbon Chemicals Company (Y-12 Plant)  
133 Chicago Patent Group  
134 Chief of Naval Research  
135 Columbia University (Hassialis)  
136 Dow Chemical Company, Pittsburgh  
137 Dow Chemical Company (Rocky Flats)  
138-142 duPont Company, Augusta  
143-145 General Electric Company (ANPP)  
146-151 General Electric Company, Richland  
152-153 Goodyear Atomic Corporation  
154 Hanford Operations Office  
155 Iowa State College  
156-159 Knolls Atomic Power Laboratory  
160-161 Los Alamos Scientific Laboratory  
162 Mallinckrodt Chemical Works  
163 Massachusetts Institute of Technology (Kaufmann)  
164 Materials Laboratory (MDC)  
165 Merrill Company  
166-168 Mound Laboratory  
169 National Advisory Committee for Aeronautics, Cleveland  
170 National Bureau of Standards  
171 National Lead Company of Ohio  
172 Naval Medical Research Institute  
173-174 Naval Research Laboratory  
175 New Brunswick Laboratory  
176-178 New York Operations Office  
179-180 North American Aviation, Inc  
181 Patent Branch, Washington  
182-185 Phillips Petroleum Company  
186 Pratt & Whitney Aircraft Division (Fox Project)  
187 Rand Corporation  
188 Rohm and Haas Company  
189 Sandia Corporation  
190 Sylvania Electric Products, Inc  
191 Tennessee Valley Authority  
192 U. S. Naval Radiological Defense Laboratory  
193 UCLA Medical Research Laboratory (Warren)  
194-197 University of California Radiation Laboratory, Berkeley  
198-199 University of California Radiation Laboratory, Livermore  
200-201 University of Rochester  
202 Virginia-Carolina Chemical Corporation  
203-204 Vitro Corporation of America  
205 Western Reserve University (Friedell)  
206-207 Westinghouse Electric Corporation  
208-222 Technical Information Service, Oak Ridge

TABLE OF CONTENTS

	PAGE
SUMMARY	5
INTRODUCTION	6
DESCRIPTION OF EXPERIMENTAL PROCEDURE	8
A    Discussion of Method	8
B    Description of Equipment	10
EXPLANATION OF THE CORRELATION	15
REFERENCES	26
APPENDIX	27
TABLE 1    Experimental Density-Temperature Data	28
TABLE 2    Constants Used in Calculating Room Temperature Densities	29
TABLE 3    Calculation of Room Temperature Densities	30
TABLE 4    Comparison of Predicted and Experimental Density-Temperature Data	37

## SUMMARY

This report contains a summary of all the experimental density measurements on molten fluoride mixtures that have been developed for the Aircraft Nuclear Propulsion Project. A correlation of these data is presented which can be used to predict liquid densities of fluoride mixtures of known composition over wide, elevated temperature ranges.

Experimental measurements were made by the buoyancy principle using a plummet suspended in the molten salts from an analytical balance, the entire system being enclosed in a dry-box.

All the information available on compositions, experimental densities, melting points and cubical coefficients of expansion may be found in this report, calculated values of liquid and room temperature densities, molecular weights and molecular volumes of all the mixtures that have been developed for the ANP program are also presented.

## INTRODUCTION

Since the outset of the Aircraft Nuclear Propulsion project, interest has been centered on molten fluoride mixtures as the best potential circulating fluids for use in high temperature reactors of the ARE type. During the course of the project, some fifty or more mixtures of fluorides have been suggested and a number of these aroused sufficient interest to merit measurements of their physical properties.

In the early stages of the density research program the experimental accuracy was somewhat lower than in the later stages. During the former period some questions concerning purity of both the molten salts and the blanketing atmosphere arose. Also, the techniques of temperature measurement and control, and weighing facilities were refined during the latter period. As a result, the more recent determinations afford a somewhat higher degree of accuracy than the earlier ones.

The correlation described in this report is based on measurements on all the mixtures that have been studied. In a few instances, notably composition No. 12 (Flinak), it has been possible to make a second set of measurements on a mixture for which the properties had been measured very early in the project, and in these instances the data listed below are the revised values. In past reports on several of the compositions, a correction based

on the volume change of the plummet with temperature was omitted, the error introduced being well within the accuracy claimed for the data. However, this correction has been applied where necessary in this report and it is suggested that in subsequent studies involving the densities of fluorides, the data in this report be used.



## DESCRIPTION OF EXPERIMENTAL PROCEDURE

### A Discussion of Method

Density values reported here were determined by the buoyancy principle involving a plummet suspended in a liquid. The density of the liquid,  $\rho$ , is defined by

$$\rho = \frac{w_L}{v_L} \quad (1)$$

where,

$w_L$ , weight of liquid displaced by the plummet

$v_L$ , volume of liquid displaced by the plummet

and

$$w_L = W_A - W_L \quad (2)$$

where,

$W_A$ , weight of plummet in air

$W_L$ , weight of plummet in liquid

Upon substituting (2) in (1), there results

$$\rho = \frac{W_A - W_L}{v_L} \quad (3)$$

The volume of liquid displaced by the plummet,  $v_L$ , is also equal to the volume of the plummet and may be determined by weighing the plummet in a liquid of known density (water was used) At room temperature the volume of the plummet is

$$v_{L_0} = \frac{W_A - W_{H_2O}}{\rho_{H_2O}} \quad (4)$$

where,

$W_{H_2O}$ , weight of the plummet in  $H_2O$  at room temperature

$\rho_{H_2O}$ , density of water at room temperature

The volume of the plummet at elevated temperatures is

$$v_L = v_{L_0} \left[ 1 + \beta_p (T - T_0) \right] = \frac{W_A - W_{H_2O}}{\rho_{H_2O}} \left[ 1 + \beta_p (T - T_0) \right] \quad (5)$$

where,

$T$ , liquid temperature

$T_0$ , room temperature

$\beta_p$ , cubical expansion coefficient of the plummet

Upon substituting equation (5) into equation (3), one obtains

$$\rho = \frac{(W_A - W_L)}{(W_A - W_{H_2O})} \frac{\rho_{H_2O}}{[1 + \beta_p (T - T_0)]} \quad (6)$$

$W_A$ ,  $W_{H_2O}$  and the temperature of water were measured before the experiment was started. Values for  $\rho_{H_2O}$  and  $\beta_p$  are known, values of  $W_L$  at the various temperatures were measured.

Experimental density data are represented in this report by the equation

$$\rho = a - bT \quad (7)$$

Values of the cubical coefficients of expansion were calculated from the defining equation

$$\beta_L = - \frac{1}{\rho} \left( \frac{d\rho}{dT} \right)_p \quad (8)$$

The experimental data are given in Table 1 and in Figure 3 where the temperature range over which measurements were made on each mixture is shown. The experimental data are also tabulated in Table 4 in the form of equation (7). A simple analysis indicates that these data are probably not in error by more than  $\pm 5\%$ . Experimental values for the coefficients of cubical expansion of the various liquids may be found in Table 1.

#### B Description of the Equipment

The system (see Figure 1) used for taking these measurements consisted principally of a stainless steel plummet suspended in the molten salts by a

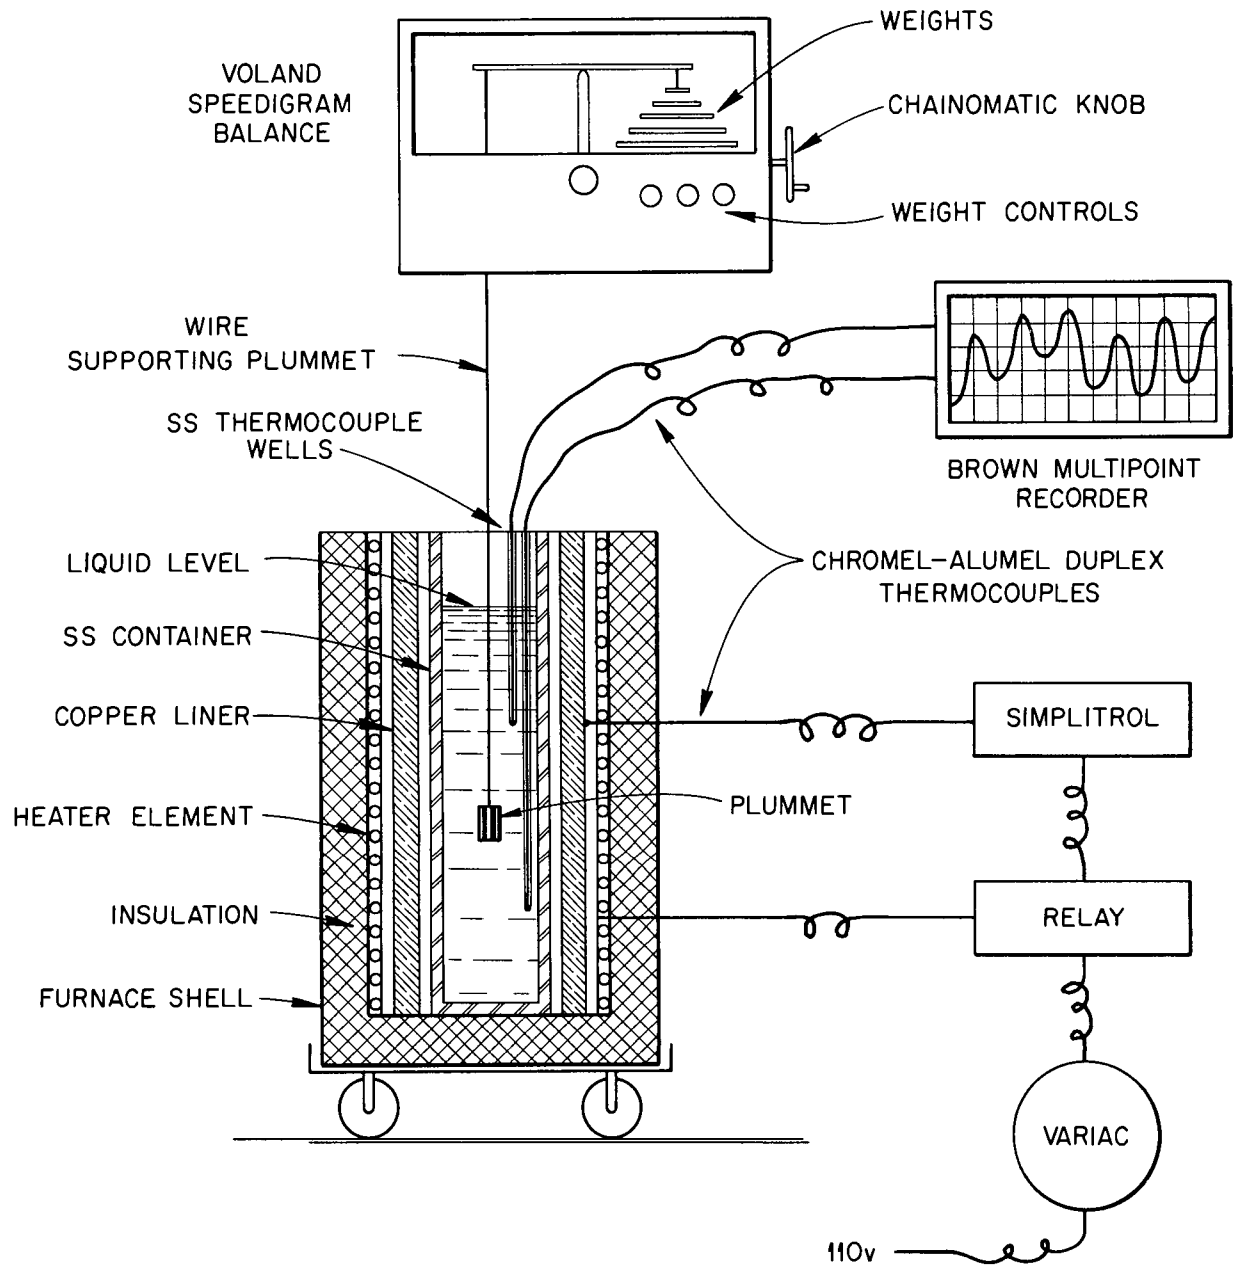


Fig 1 Schematic Diagram of Density Measurement System

UNCLASSIFIED  
PHOTO 21571

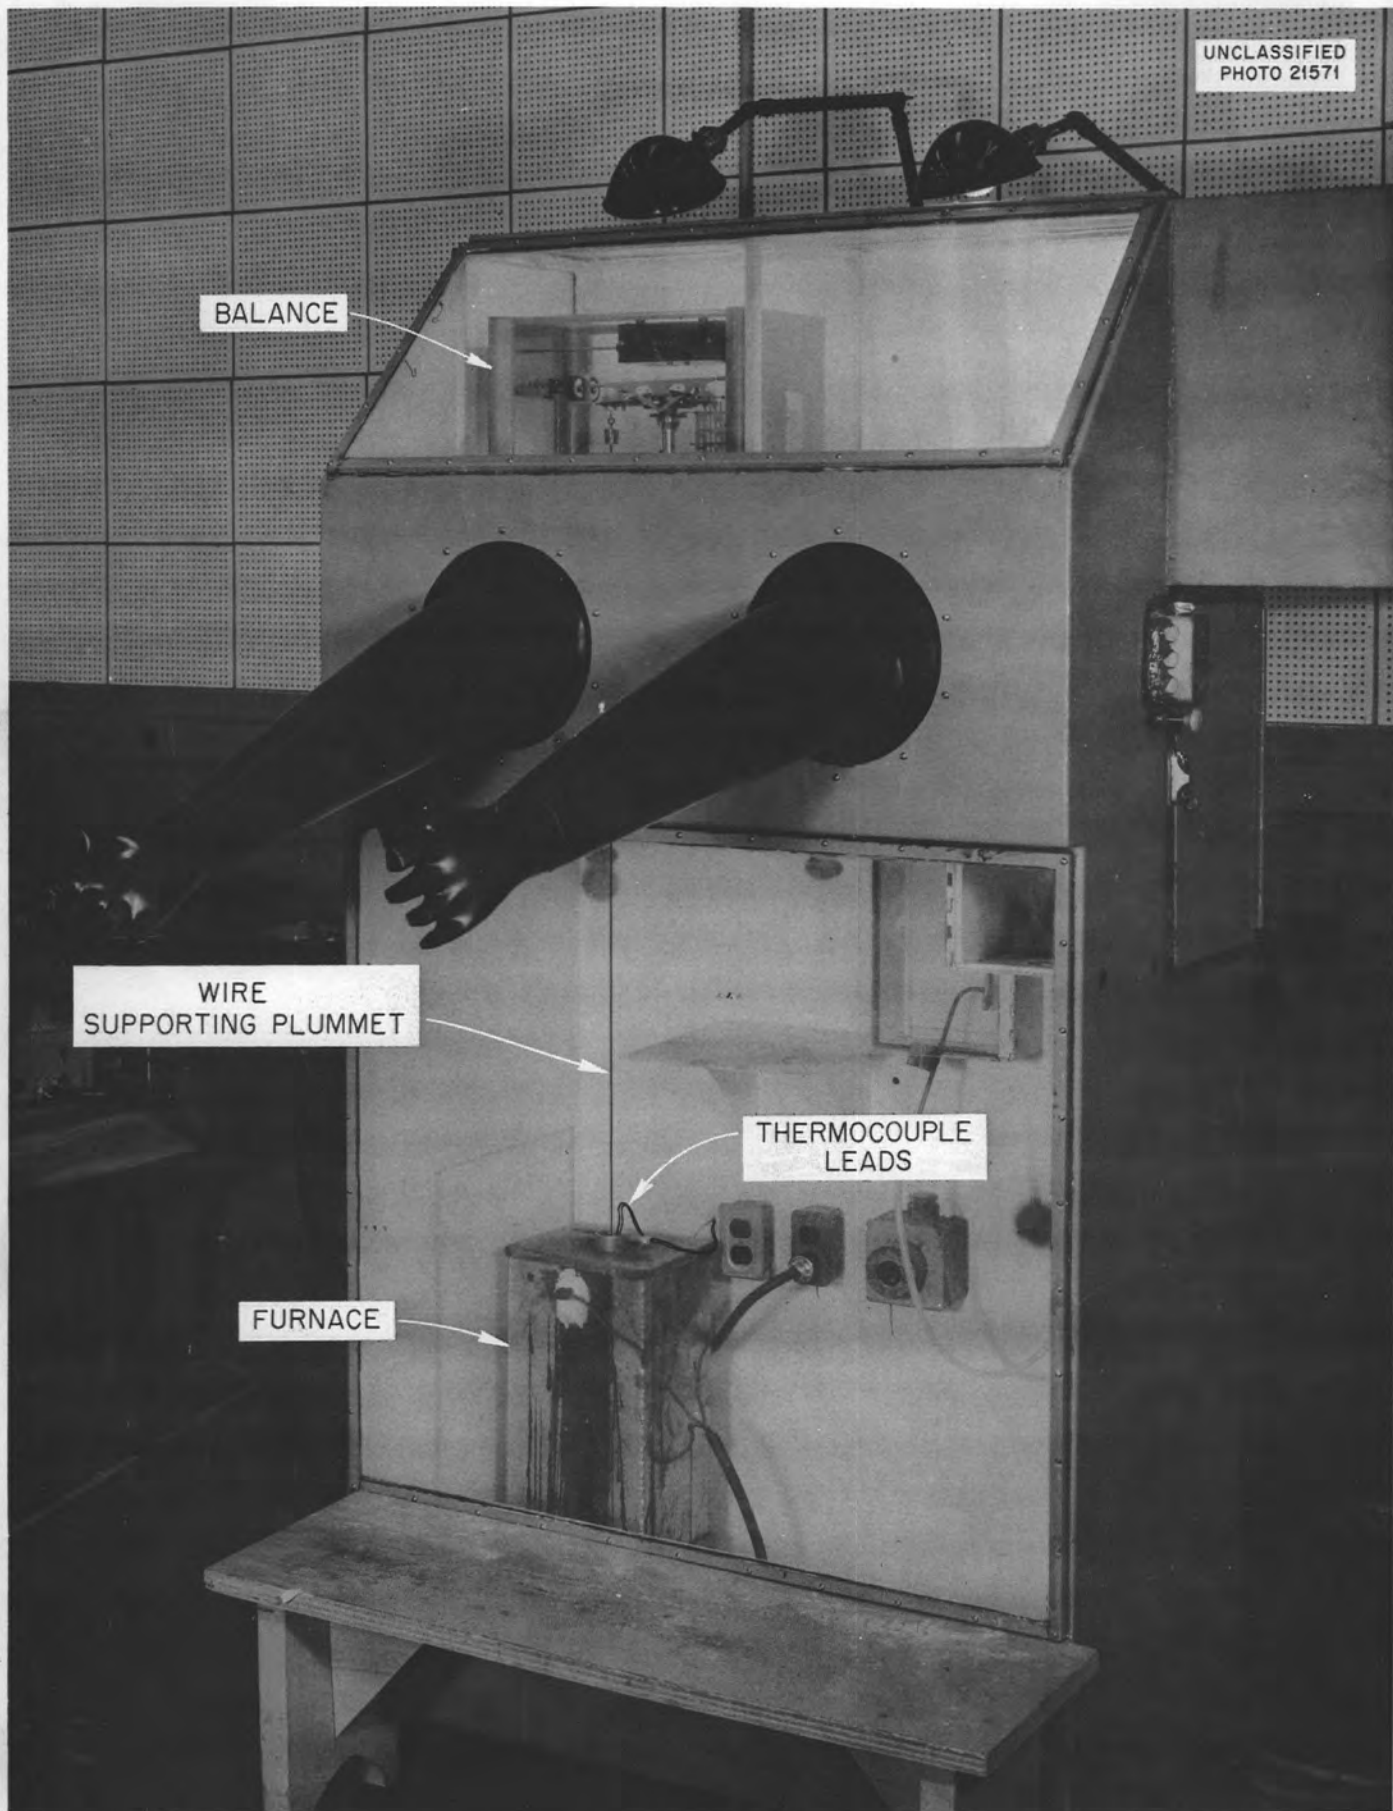


Fig. 2. Photograph of Dry Box Containing Density Measurement System.

fine steel wire from a Volland 'Speedigram' balance (a chainomatic balance on which weights larger than 100 mg are controlled mechanically by knobs with no loss in accuracy) The plummets were fabricated from 1/4" No 316 stainless steel rod The containers for the molten salts were fabricated from 1 1/2' I P S , Schedule 40, No 316 stainless steel pipe The tube furnace was mounted on a small rolling platform equipped with ball-bearing casters to facilitate centering of the tube under the balance as well as under the two systems for determining viscosities which were also housed in the dry-box (Both density and viscosity measurements were made during the same heat-up period Viscosity studies will be discussed in a separate report)

The temperature of the melt was measured with the aid of two chromel-alumel thermocouples and a Brown multipoint recorder, the couples were inserted in wells made of 1/8' stainless tubing and supported in the liquid salt so that one couple was 2-3 inches below the surface and the other 5-6 inches below the surface The wire supporting the plummet was of such length that the plummet was suspended at a depth between the two couples Temperature of the furnace was controlled by a combination of a variac and a Simplitrol with a chromel-alumel thermocouple The hot junction of this couple was imbedded in the outside surface of a thick-walled copper pipe used as a thermal diffuser between the heating surfaces of the tube furnace and the tube containing the melt Since this hot junction "sees" the heating element face, a very sensitive temperature control was afforded As the experiment progressed, the temperature setting was increased by a small



increment and in a short time the temperatures indicated by the two immersed thermocouples rose to a point slightly below that set on the Simplitrol, leveled off and approached each other, at this point the two readings were usually no more than 5 degrees apart. After this practically isothermal condition was reached, a weight reading and the average temperature were recorded.

Since the fluorides in the molten state are very sensitive to the atmosphere, a number of precautions were taken to insure its purity. Argon was circulated through the dry-box and out of a bubbler at a measured rate until the calculated concentration of argon was above 99.9%. These calculations have been checked experimentally by measuring the oxygen concentration of the gas in the dry-box with a Burrell Gas Analyzer. Effort was made to remove the final traces of oxygen and water, these being the chief undesirable impurities, by placing indicating Drierite from a closed container into a flat open dish to get the water and by starting up an oxygen removal device consisting of a tube furnace containing a cartridge of copper filings and equipped with a 15 CFM blower. The filings were brought to red heat and the atmosphere in the dry-box circulated over them. Purity of the atmosphere, which determines the purity of the melt, is indicated by the appearance of the plummet when it is withdrawn from the melt. The plummet, though discolored, will have a clean smooth surface when taken from a clean melt. No difficulty was encountered with condensation on the wire except during measurements on mixtures containing  $ZrF_4$ . When working with these salts, the plummet was removed between weighings and the tube containing the melt was covered to retard the zirconium snow effect.

# EXPLANATION OF THE CORRELATION

Although more than fifty different fluoride mixtures have been developed since the initiation of the ANP program, density measurements have been made on only fifteen of these mixtures. In addition, new mixtures are developed as the program continues. For these reasons it was felt that a method for predicting densities of molten fluorides would be useful and the correlation described below was developed.

The correlation is based on plots of the experimentally determined liquid densities at any one temperature against the calculated densities of the corresponding mixture at room temperature. These room temperature densities are calculated by the formula

$$\rho = \frac{\sum_{i=1}^N M_i f_i}{\sum_{i=1}^N (M_i / \rho_i) f_i} \quad (9)$$

where,

$\rho$ , density at room temperature of the mixture  
(gm/cc)

$M_i$ , molecular weight<sup>1</sup> of a component of the  
mixture (gm/mol)

$f_i$ , mol fraction of that component

$\rho_i$ , density at room temperature<sup>1</sup> of that component  
(gm/cc)

---

<sup>1</sup>The values used for the various components are listed in Table 2 of the appendix

The numerator is the calculated molecular weight of the mixture and the denominator is the calculated molecular volume of the mixture. Values of the room temperature density calculated from this formula were checked against experimentally determined values for a series of 10 fluoride mixtures and were found to differ by no more than  $\pm 5$  percent (Reference 1)

Figure 3 gives the density-temperature data for all of the liquid fluoride mixtures that have been studied to date (References 2, 3, 4, 5, 6, 7, 8, 9, 10, 11, 12). The figures in parentheses are the calculated room temperature densities. The data given in Table 1 were used in drawing these curves. It is noted that the average liquid densities are proportional to the calculated room temperature densities of the corresponding mixtures.

Figures 4a, 4b, 4c and 4d represent plots of liquid densities against the calculated room temperature densities of corresponding mixtures at  $600^{\circ}\text{C}$ ,  $700^{\circ}\text{C}$ ,  $800^{\circ}\text{C}$  and  $900^{\circ}\text{C}$  respectively, these isotherms were cross-plotted from Figure 3. Figure 5 is a composite of figures 4a, 4b, 4c and 4d. Knowing only the calculated room temperature density, the liquid density may be predicted for any mixture of fluorides over this temperature range.

Figures 6 and 7 were derived from Figure 5 and give the constants,  $a$  and  $b$ , for equation 7, as a function of the room temperature density.

The density correlation presented here satisfactorily represents all the experimental measurements on the fluoride mixtures, the mean deviation is about 3% and the maximum deviation is 6%. Table 3 gives the calculated room

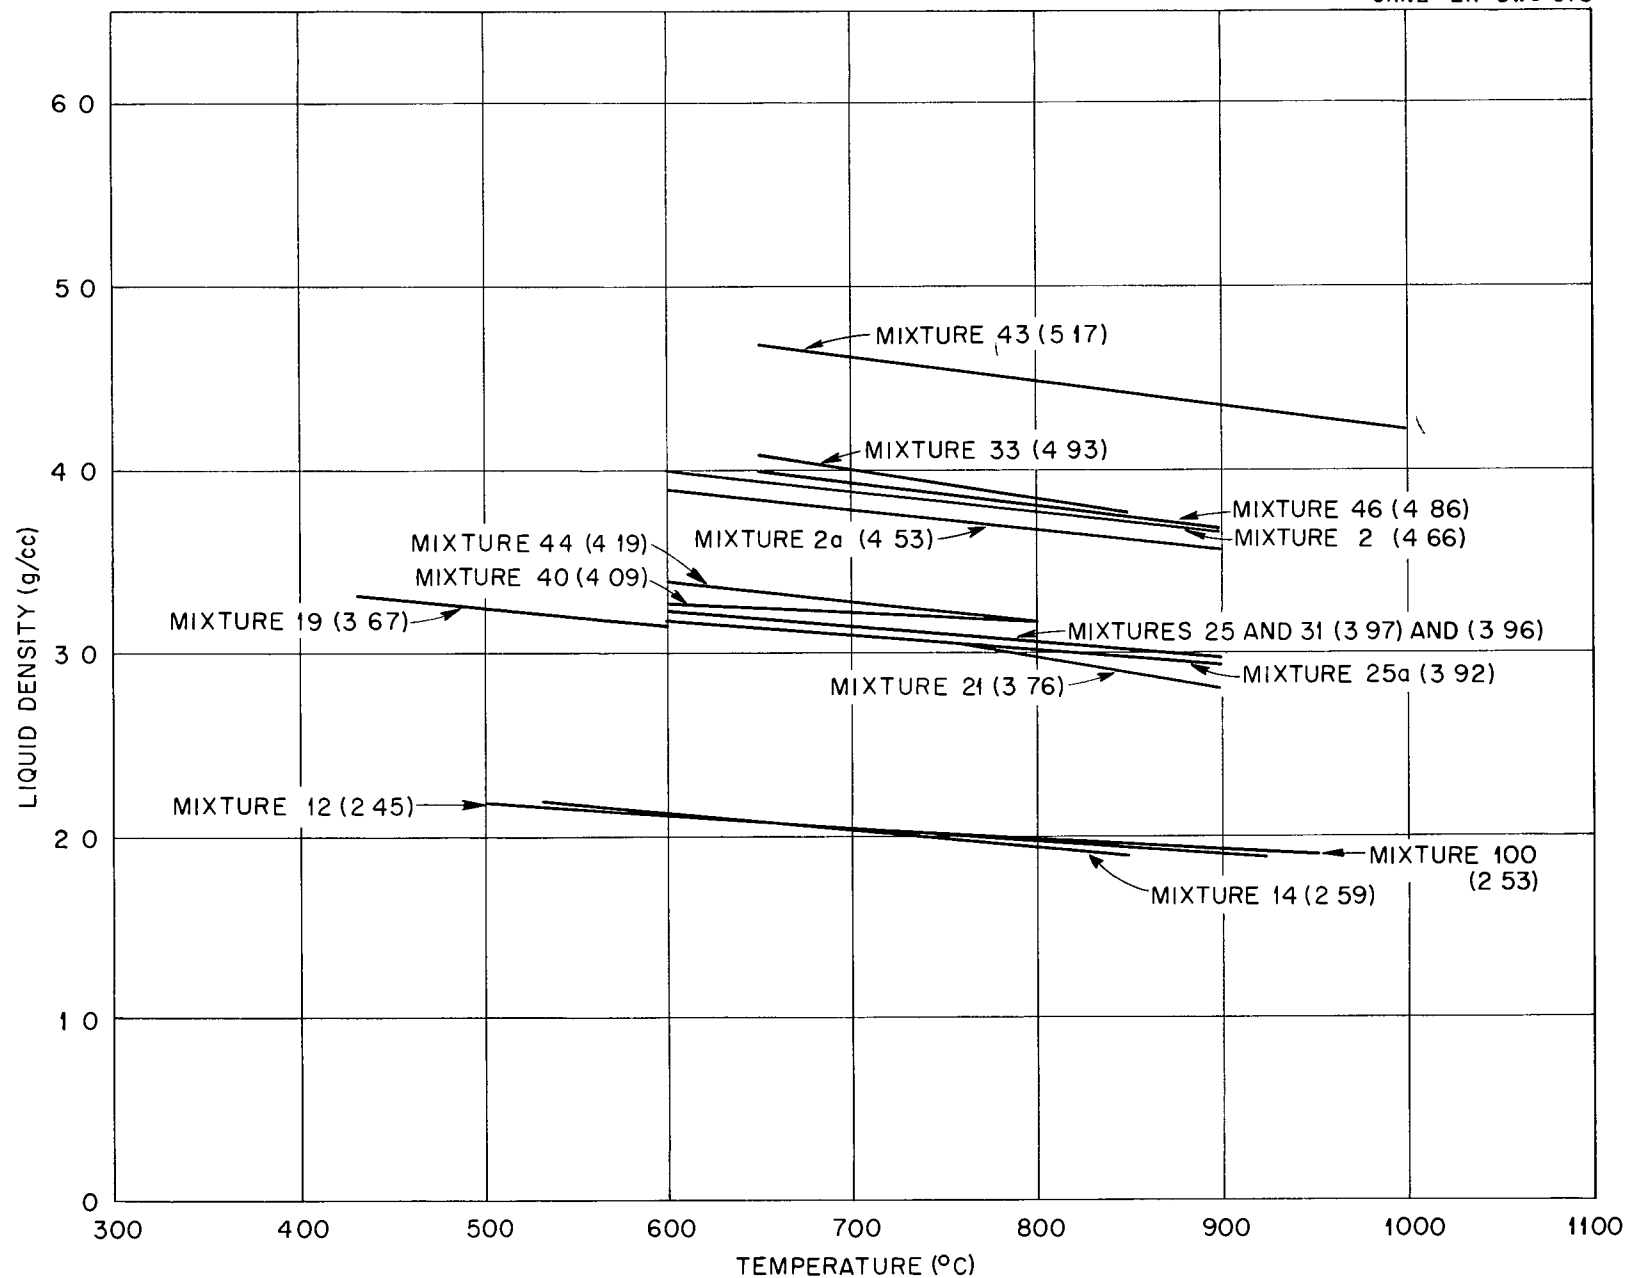


Fig 3 Densities of Fluoride Mixtures (g/cc) vs Temperature (°C)(Numbers in Parentheses are Calculated Room Temperature Densities)

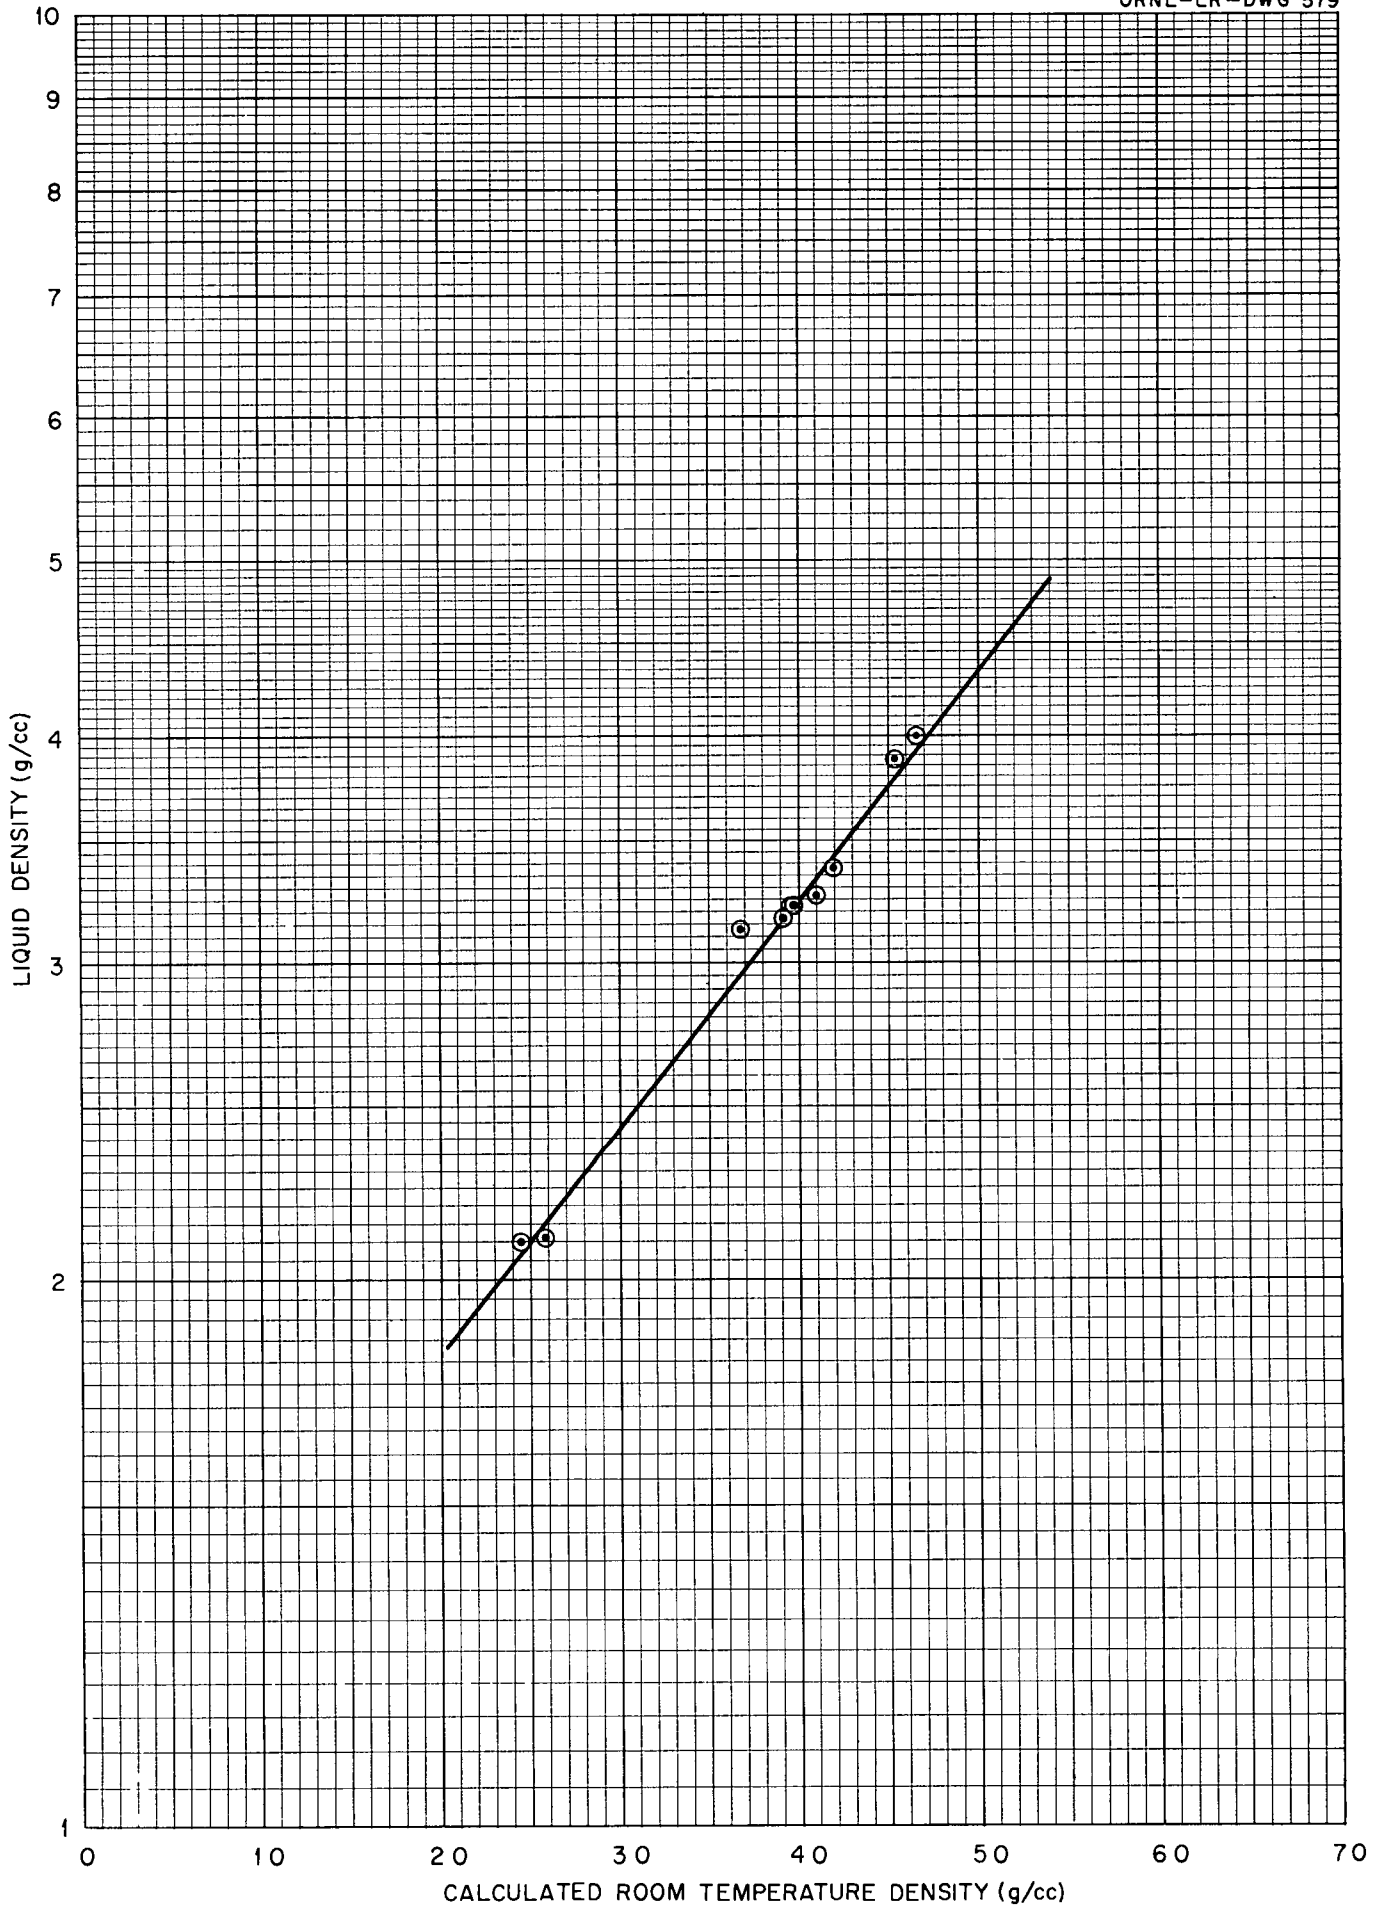


Fig 4a Liquid Density at 600°C vs Calculated Room Temperature Density

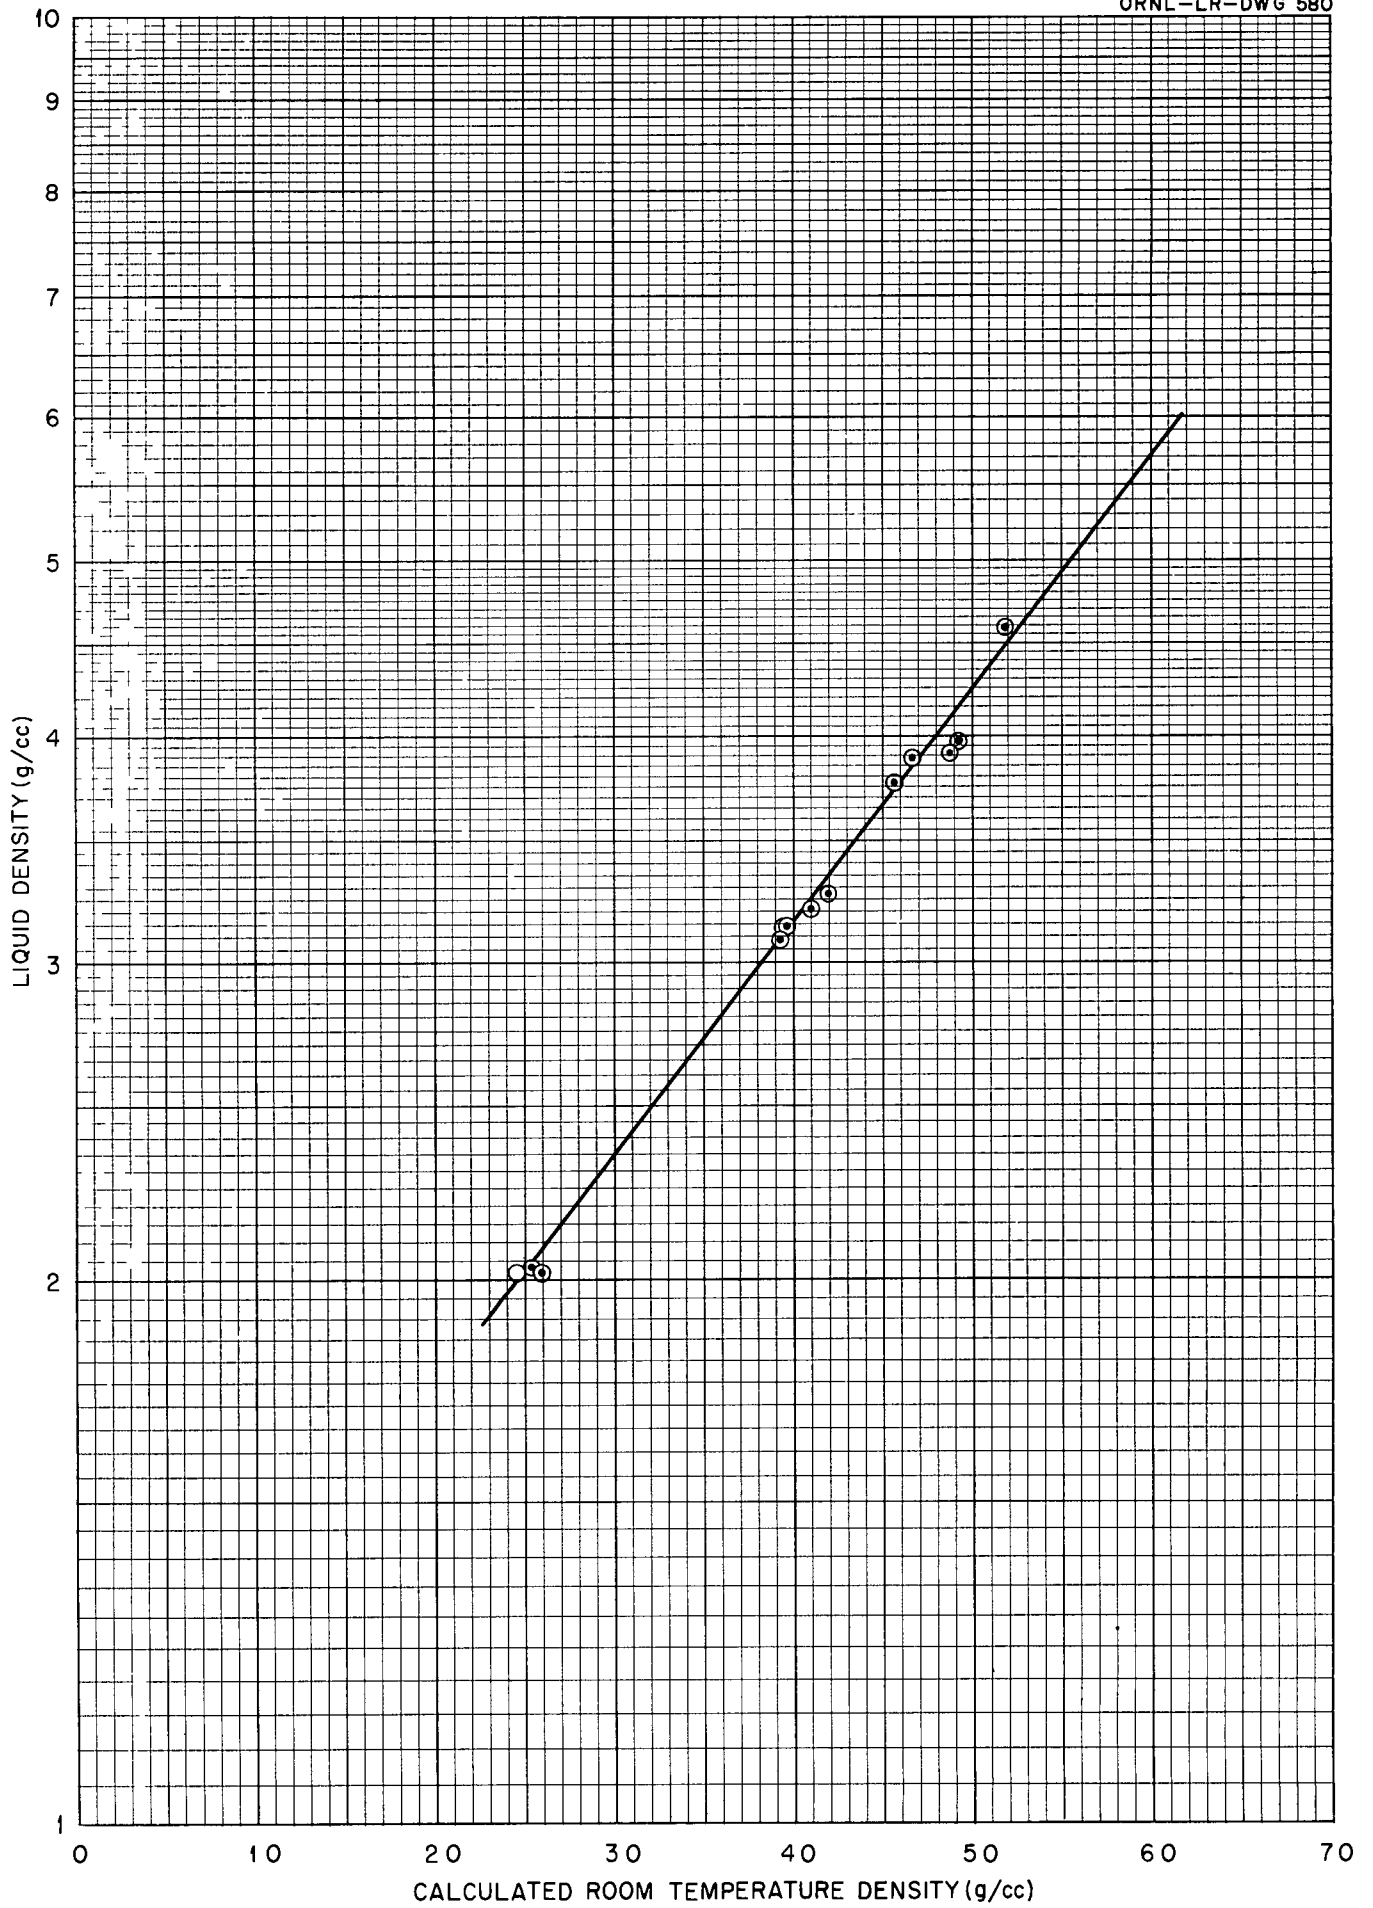


Fig 4b Liquid Density at 700° C vs Calculated Room Temperature Density



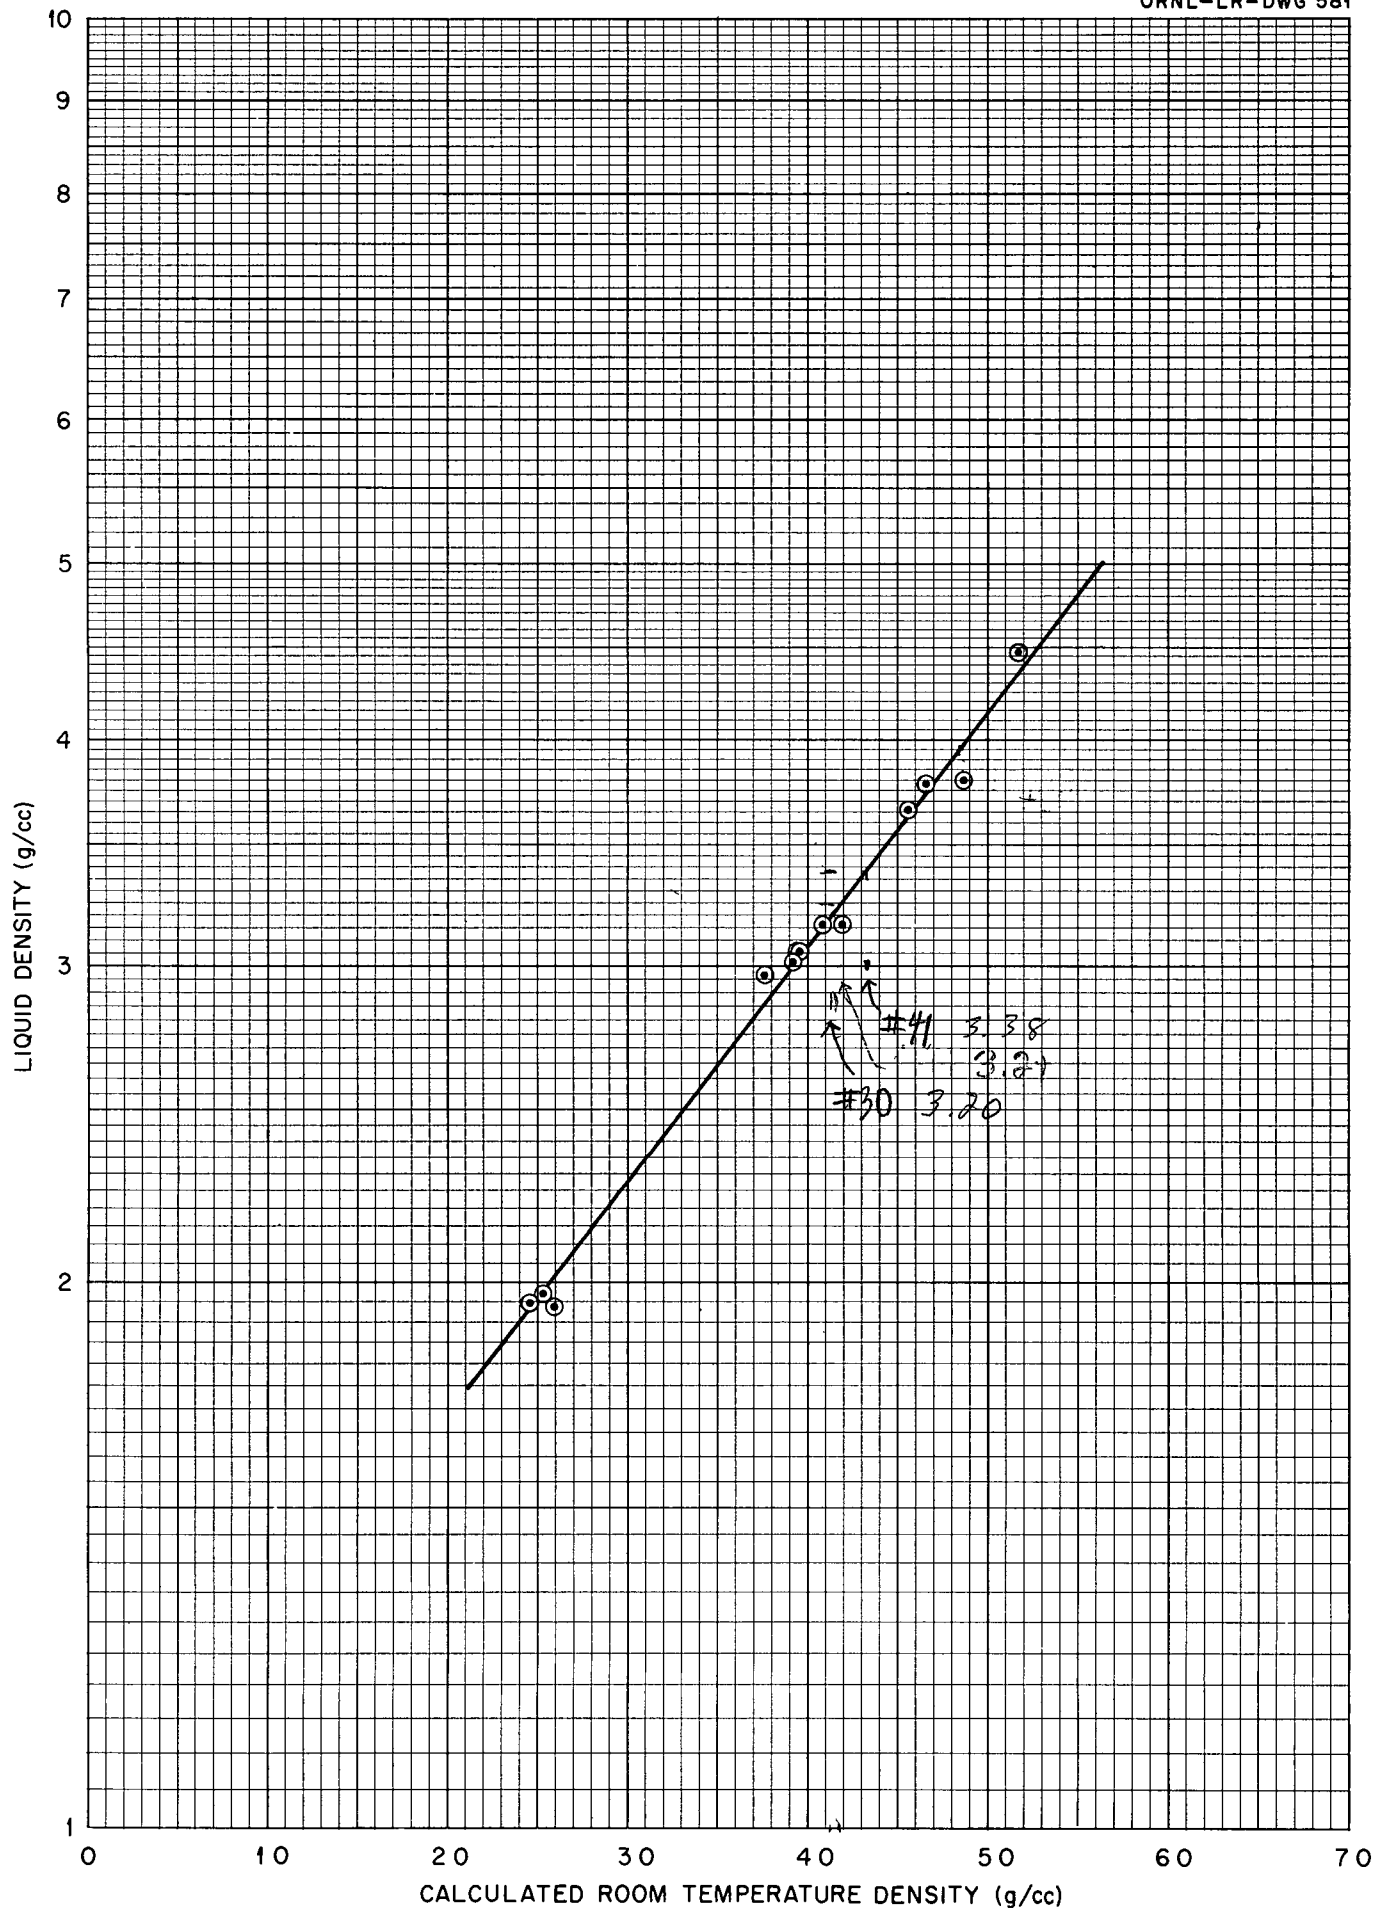


Fig 4c Liquid Density at 800°C vs Calculated Room Temperature Density

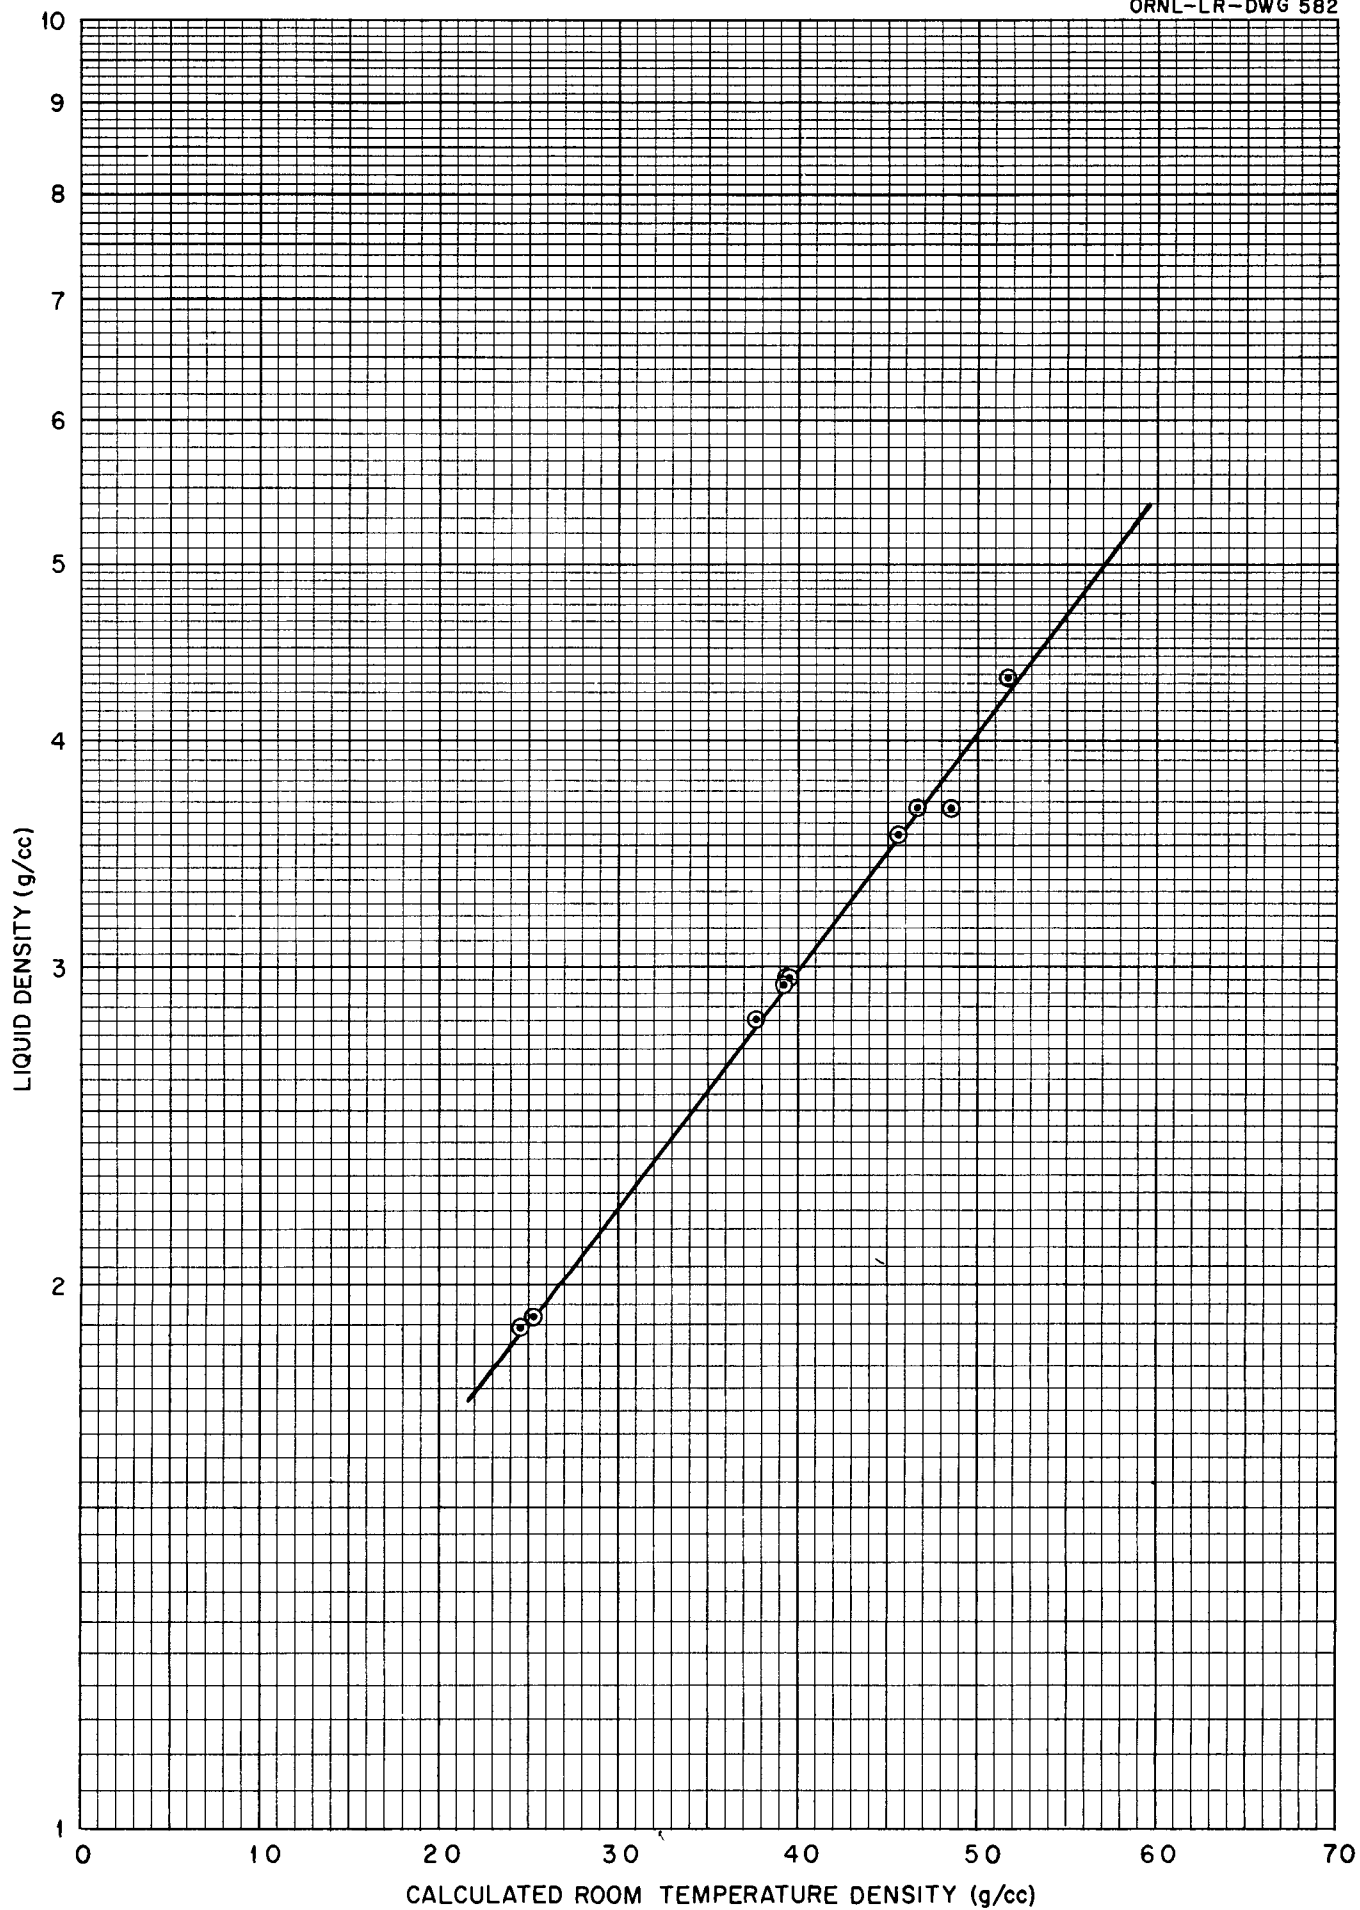


Fig 4d Liquid Density at 900° C vs Calculated Room Temperature Density

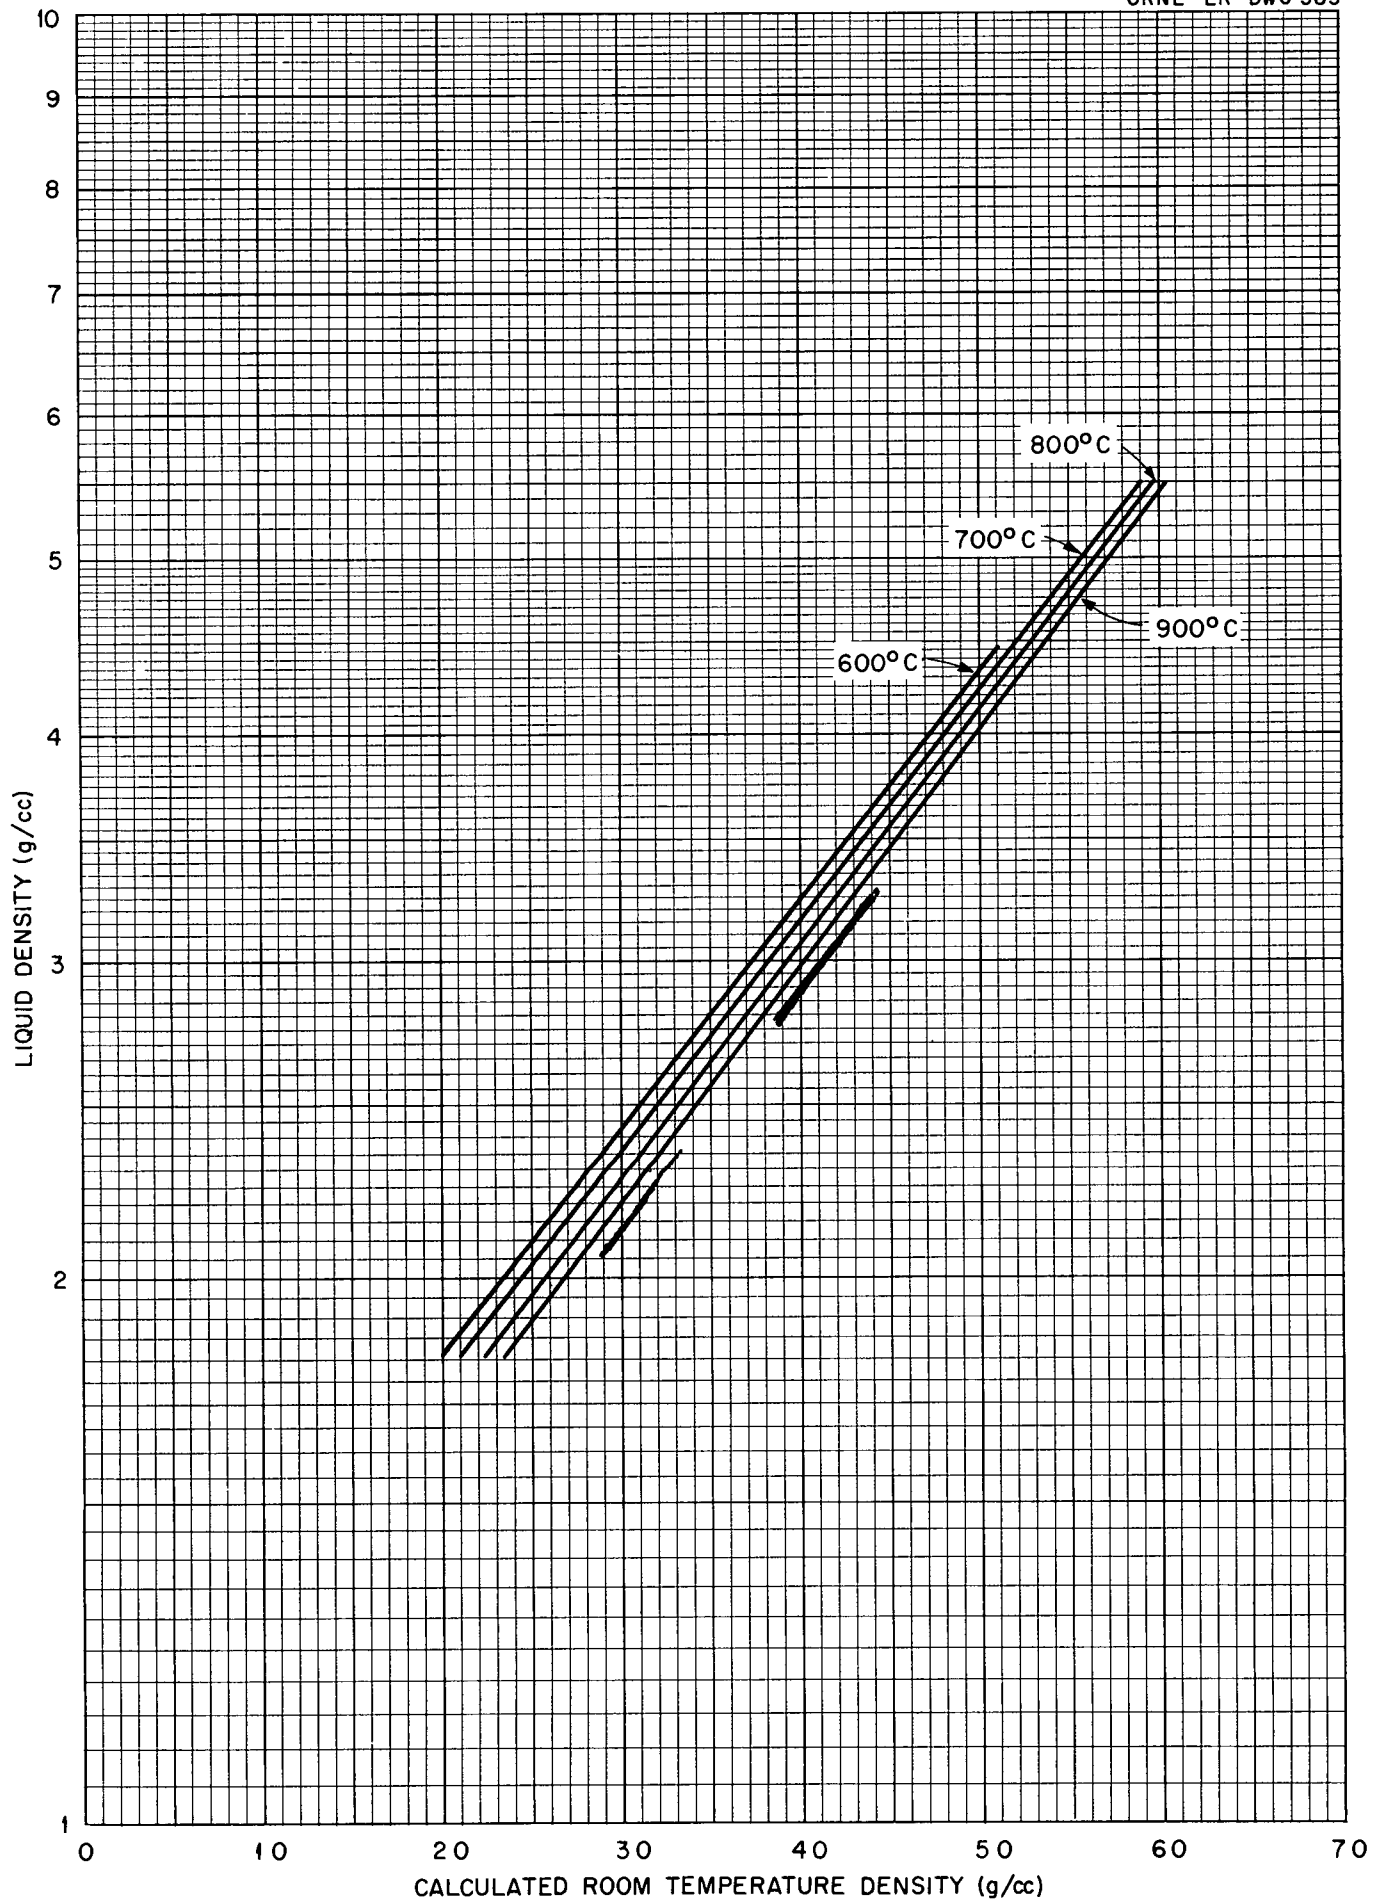


Fig 5 Liquid Density vs Calculated Room Temperature Density (Composite of Figures 2a 2b 2c 2d)

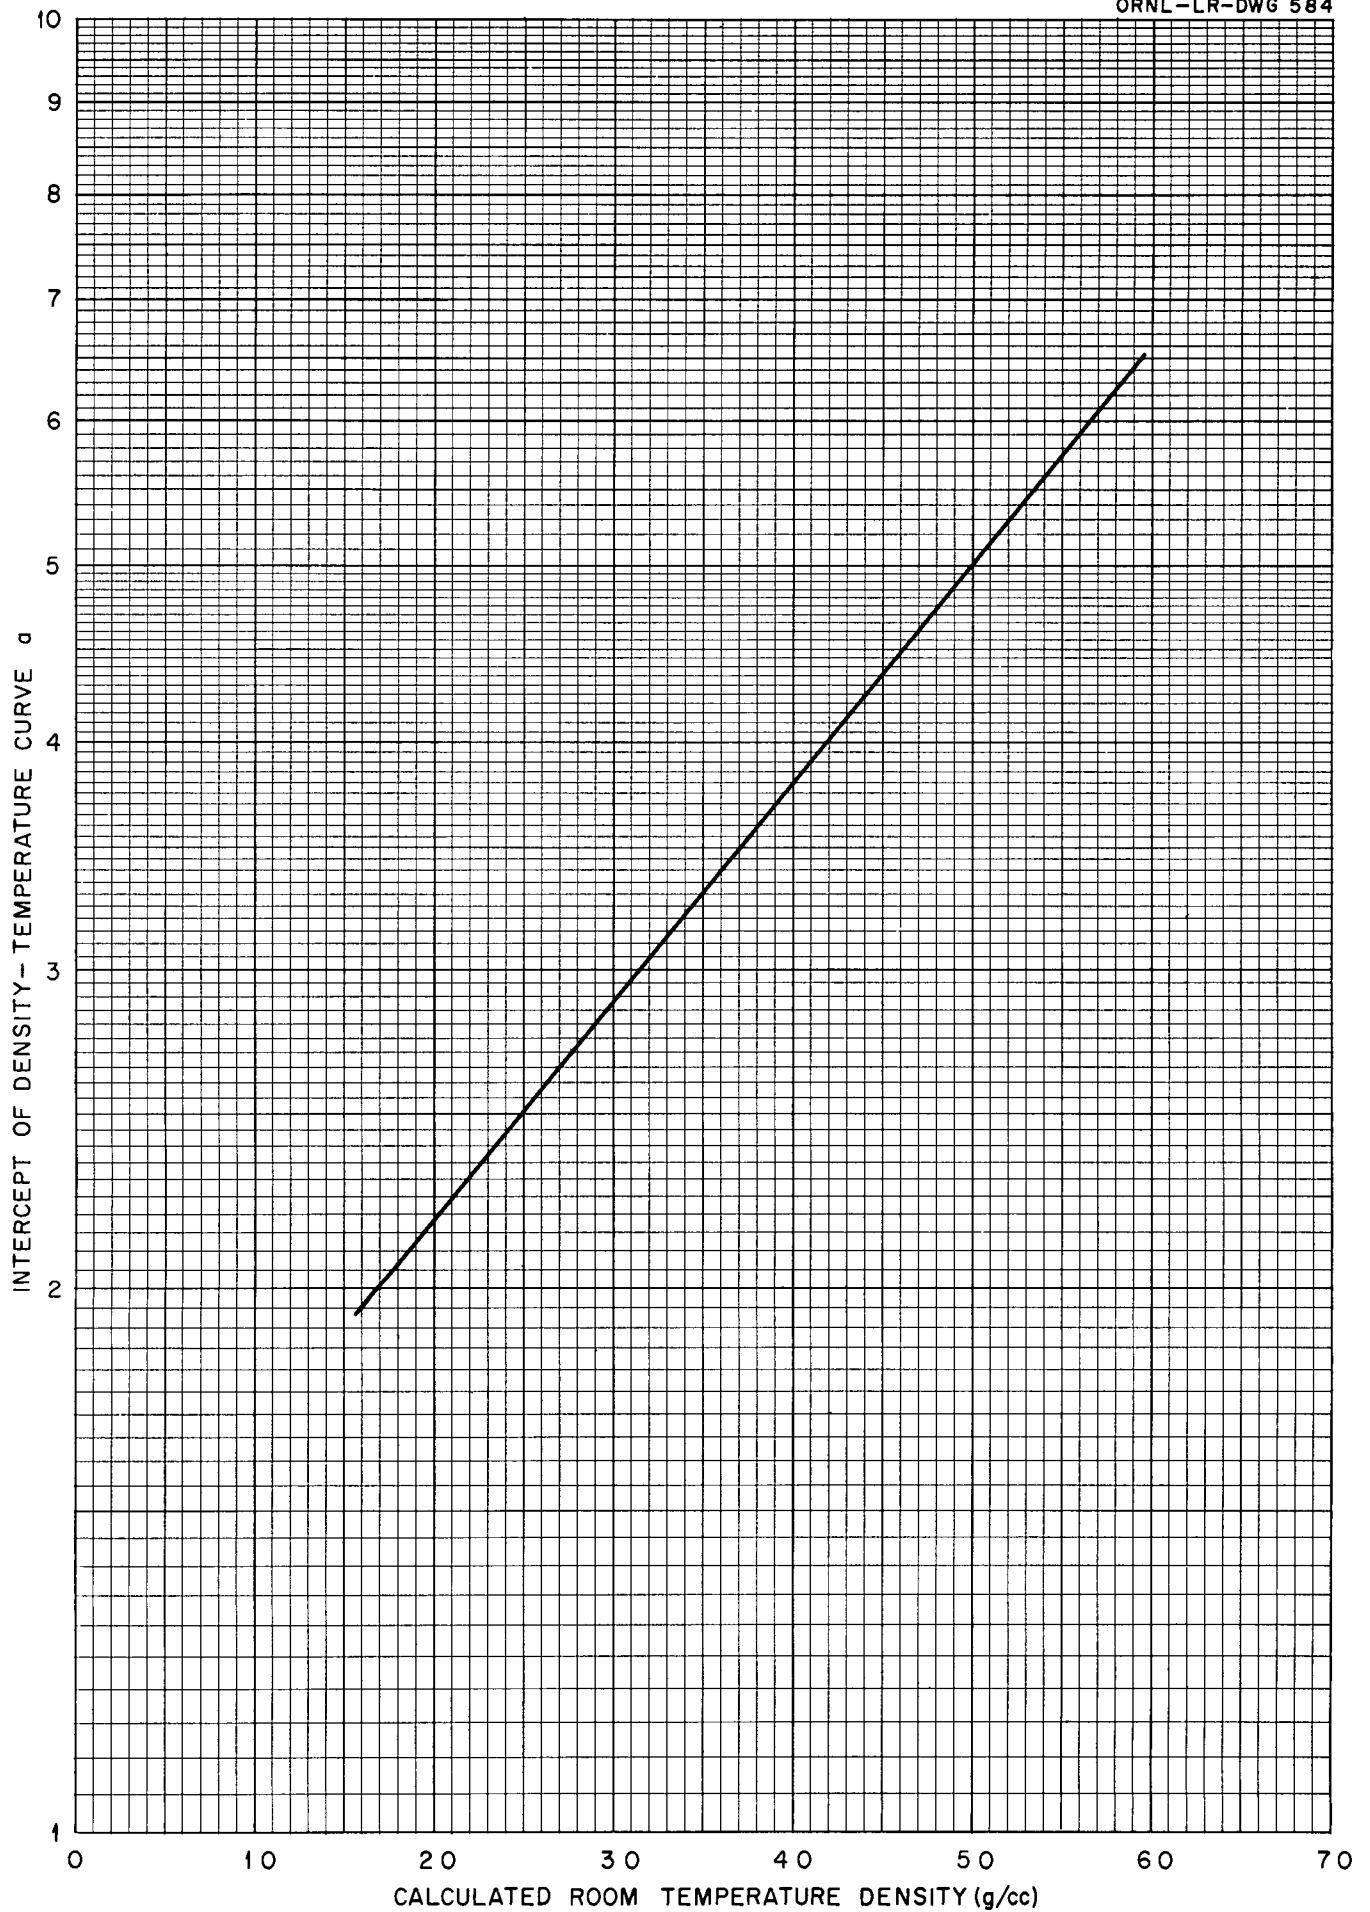


Fig 6 Intercept of Density-Temperature Curve ( a ) vs Calculated Room Temperature Density

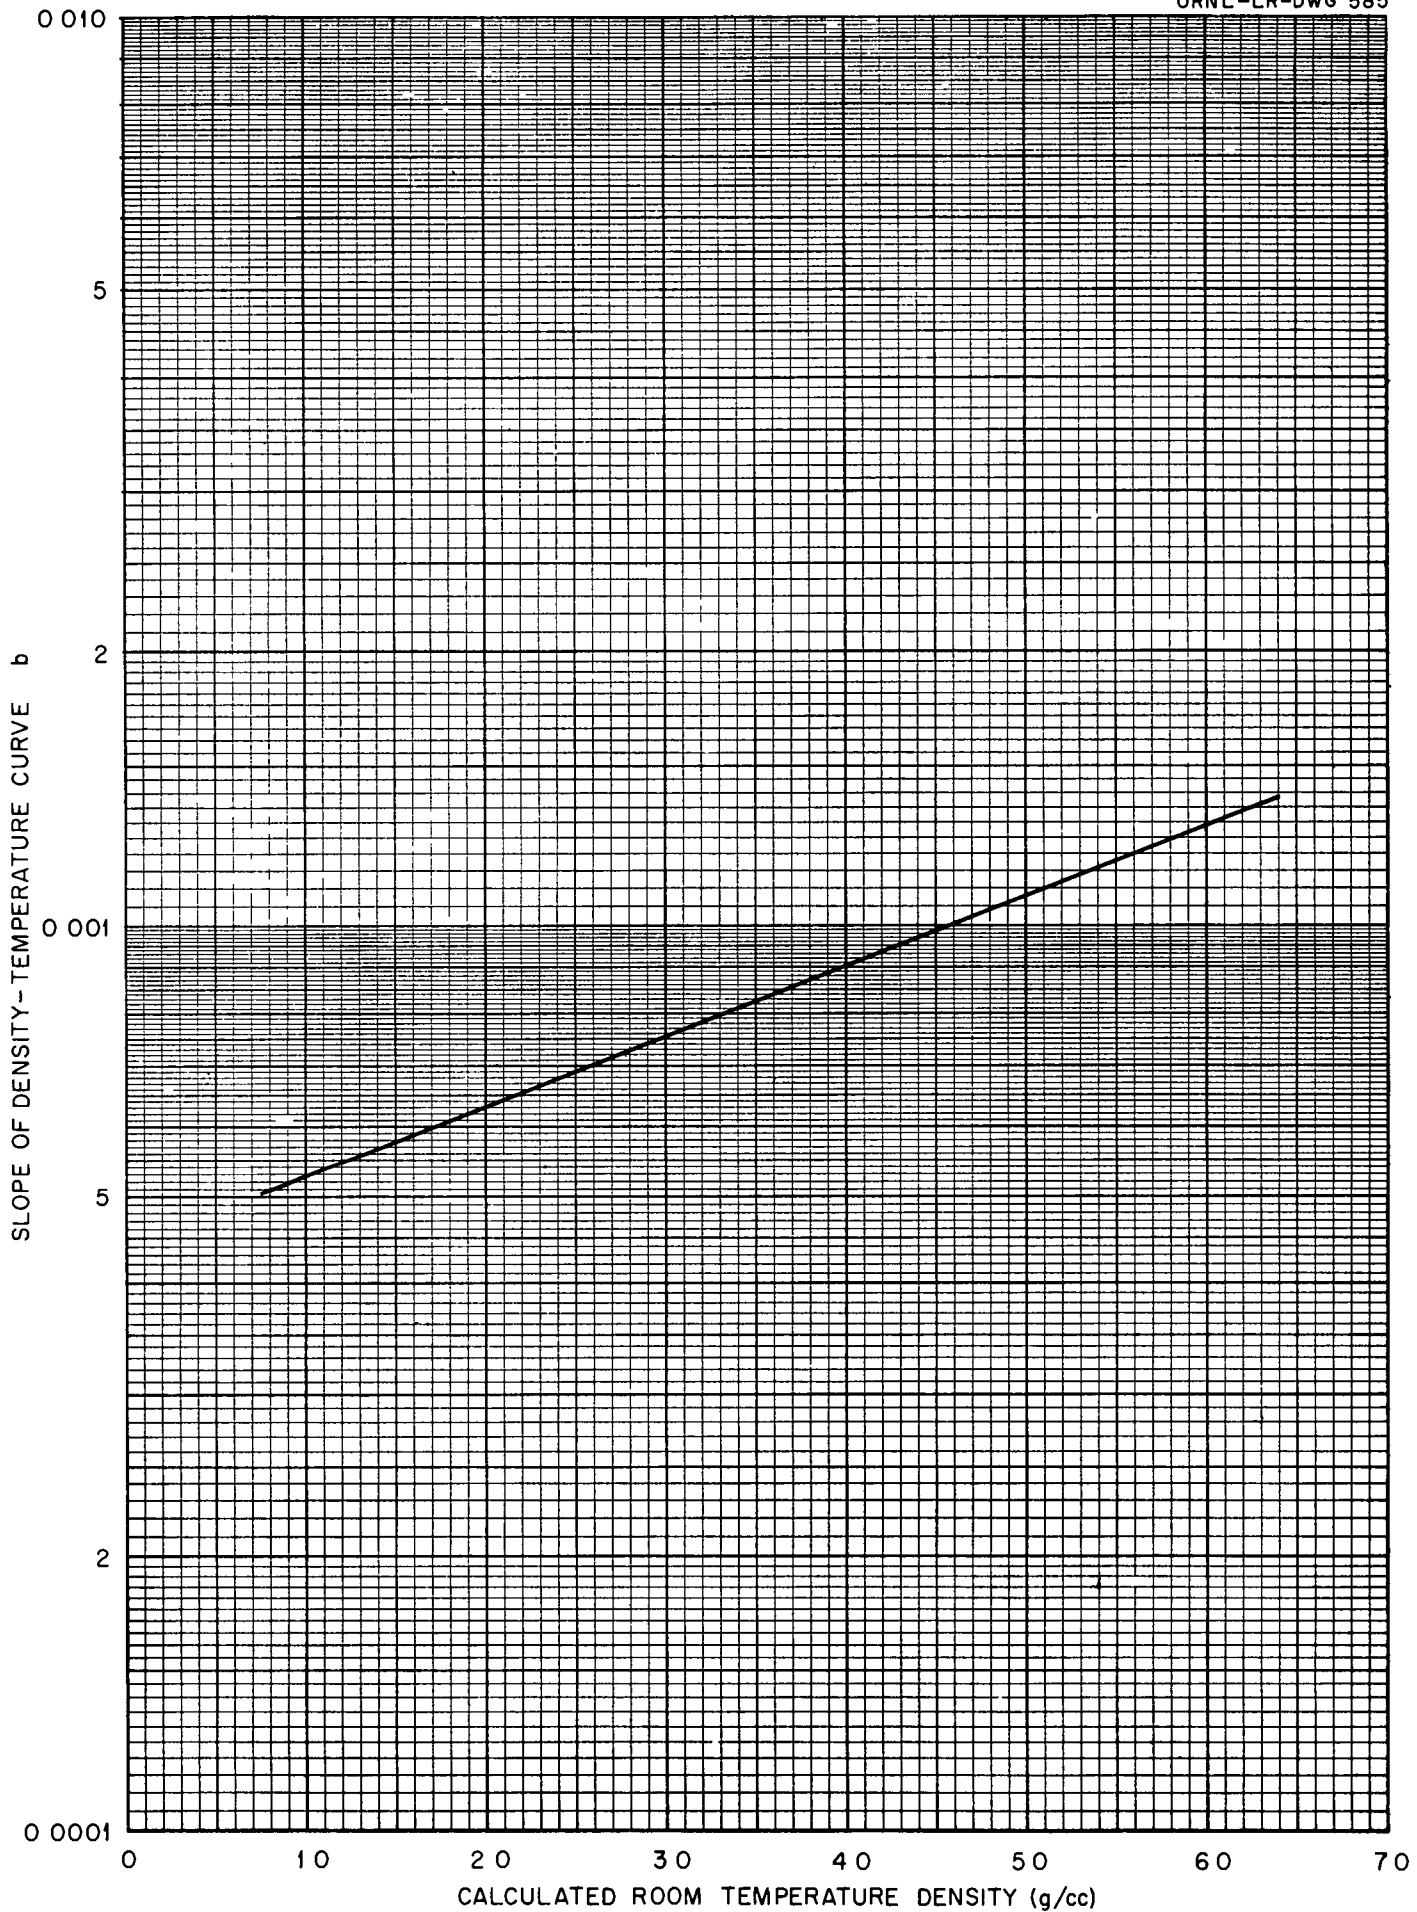


Fig 7 Slope of Density-Temperature Curve( b ) vs Calculated Room Temperature Density

temperature densities, as well as compositions, molecular weights and molecular volumes, for all the fluoride mixtures that have been formulated in the ANP program (References 13 and 14) and Table 4 lists the predicted densities in terms of equation 7 for all of these mixtures as well as the experimentally determined formulae to illustrate the agreement

Cubical coefficients of expansion at 700°C of the liquids calculated from this correlation are inversely proportional to density and vary from  $3.60 \times 10^{-4}$  (1/°C) for a mixture having a room temperature density of 2.0 (gm/cc) to  $2.37 \times 10^{-4}$  (1/°C) for a mixture having a room temperature density of 5.5 (gm/cc)



REFERENCES

- 1 Melvin Tobias, S I Kaplan, S J Claiborne, ORNL CF 52-3-230
- 2 S I Kaplan, ORNL CF 51-8-97
- 3 J Cisar, ORNL CF 51-11-78
- 4 J Cisar, ORNL CF 51-11-198
- 5 J Cisar, Personal communication
- 6 R F Redmond, T N Jones, ORNL CF 52-11-105
- 7 S I Cohen, T N Jones, ORNL CF 53-7-125
- 8 S I Cohen, T N Jones, ORNL CF 53-10-86
- 9 S I Cohen, T N Jones, ORNL CF 53-8-217
- 10 S I Cohen, T N Jones, ORNL CF 53-12-179
- 11 S I Cohen, T N Jones, Memo to be issued
- 12 ANP Physical Properties Group, ORNL CF 53-3-261
- 13 C J Barton, ORNL CF 53-10-78
- 14 C J Barton, Personal communications
- 15 Katz and Rabinowitch, "The Chemistry of Uranium,"  
N N E S VIII-5, p 366
- 16 Henglein, F A , Z Elektrochem , Vol 30, p 5, 1924

APPENDIX

TABLE 1	Experimental Density-Temperature Data
TABLE 2	Constants used in Calculating Room Temperature Densities
TABLE 3	Calculation of Room Temperature Densities
TABLE 4	Comparison of Predicted and Experimental Density-Temperature Data

TABLE 1  
EXPERIMENTAL DENSITY-TEMPERATURE DATA

Composition	LIQUID DENSITY (gm/cc)				Cubical Coefficient of Expansion <sup>2</sup> 1/°C x 10 <sup>4</sup>	Reference
	600°C	700°C	800°C	900°C		
2	4 00	3 89	3 78	3 67	2 96	2,12
2a	3 88	3 77	3 66	3 55	2 92	3,12
12	2 10	2 02	1 94	1 88	3 61	11
14	2 11	2 02	1 93		4 46	4,12
19	3 13				3 48(600°C)	5,12
21			2 96	2 80	5 51(800°C)	5,12
25	3 23	3 14	3 05	2 96	2 90	5,12
25a	3 17	3 09	3 01	2 93	2 59	5,12
31	3 23	3 14	3 05	2 96	2 96	6,12
33		3 98			3 99	6,12
40	3 27	3 21	3 16		1 71	7
43		4 60	4 47	4 34	2 83	8
44	3 38	3 27	3 16		3 36	9
46		3 91	3 79	3 67	3 07	10
100		2 03	1 97	1 92	2 71	11

<sup>2</sup> Value is for 700°C unless otherwise noted. The calculated range of cubical expansion coefficients is from  $3.6 \times 10^{-4}$  1/°C to  $2.4 \times 10^{-4}$  1/°C. The few experimental values which fall outside of this range probably do so because they are based on early or incomplete sets of data.

TABLE 2  
CONSTANTS USED IN CALCULATING ROOM  
TEMPERATURE DENSITIES

Component	Molecular Weight, $M_1$ (gm/mol)	Room Temperature Density, $\rho_1$ (gm/cc)	Molecular Volume, $M_1/\rho_1$ (cc/mol)
LiF	25 9	2 30	11 26
NaF	42	2 79	15 05
BeF <sub>2</sub>	47	1 98	23 74
KF	58 1	2 48	23 43
ZrF <sub>4</sub>	167 2	4 43	37 74
UF <sub>4</sub>	314 1	6 70 <sup>3</sup>	46 88
RbF	104 5	3 557 <sup>4</sup>	29 38
PbF <sub>2</sub>	245 2	8 24	29 75
ThF <sub>4</sub>	308 1	6 70 <sup>5</sup>	45 99
UF <sub>3</sub>	295 1	8 95 <sup>6</sup>	32 97

<sup>3</sup>Reference 15

<sup>4</sup>Reference 16

<sup>5</sup>Value for UF<sub>4</sub> Value for ThF<sub>4</sub> not available

<sup>6</sup>Derived from X-ray data

All other values taken from Lange's Handbook  
of Chemistry, Eighth Edition

TABLE 3

CALCULATION OF ROOM TEMPERATURE  
DENSITIES OF FLUORIDE MIXTURES

$$\rho_{\text{Room Temp}} = \frac{\text{Mol Wt of Mixture}}{\text{Mol Vol of Mixture}} = \frac{\sum_{i=1}^N M_i f_i}{\sum_{i=1}^N (M_i / \rho_i) f_i} \quad \text{where,}$$

$M_i$ , molecular wt of component  
 $f_i$ , mol % of that component  
 $\rho_i$ , density at room temperature of that component

Mixture	Component	$f_i$	$M_i f_i$	Mol Wt of Mixture	$(M_i / \rho_i) f_i$	Mol Vol of Mixture	$\rho_{\text{Room Temp}}$
1	BeF <sub>2</sub>	12	5 6	75 2	2 85	19 92	3 77
	NaF	76	31 9		11 44		
	UF <sub>4</sub>	12	37 7		5 63		
2	NaF	46 5	19 5	121 0	7 00	25 98	4 66
	KF	26 0	15 1		6 09		
	UF <sub>4</sub>	27 5	86 4		12 89		
2a	NaF	48 2	20 2	114 3	7 25	25 25	4 53
	KF	26 8	15 6		6 28		
	UF <sub>4</sub>	25 0	78 5		11 72		
3	BeF <sub>2</sub>	60 0	28 2	85 8	14 24	25 03	3 43
	NaF	25 0	10 5		3 76		
	UF <sub>4</sub>	15 0	47 1		7 03		
4	NaF	35	14 7	167 6	5 27	31 06	5 40
	KF	20	11 6		4 69		
	UF <sub>4</sub>	45	141 3		21 10		
5	NaF	60	25 2	135 0	9 03	23 84	5 66
	PbF <sub>2</sub>	23	56 4		6 84		
	UF <sub>4</sub>	17	53 4		7 97		
6	NaF	30	12 6	46 1	4 52	21 12	2 18
	BeF <sub>2</sub>	65	30 6		15 43		
	KF	5	2 9		1 17		

TABLE 3 (Con't )  
CALCULATION OF ROOM TEMPERATURE  
DENSITIES OF FLUORIDE MIXTURES

Mixture	Component	$f_i$	$M_i f_i$	Mol Wt of Mixture	$(M_i/\rho_i)f_i$	Mol Vol of Mixture	$\rho_{\text{Room Temp}}$
7	NaF	50	21	126 8	7 53	26 28	4 83
	KF	20	11 6		4 69		
	UF <sub>4</sub>	30	94 2		14 06		
8	NaF	100		42			2 79 <sup>7</sup>
9	BeF <sub>2</sub>	100		47			1 98 <sup>7</sup>
10	LiF	100		25 9			2 30 <sup>7</sup>
11	KF	100		58 1			2 48 <sup>7</sup>
12 (Flinak)	NaF	11 5	4 8	41 2	1 73	16 81	2 45
	KF	42 0	24 4		9 84		
	LiF	46 5	12 0		5 24		
13	NaF	53	22 3	128	7 98	25 52	5 02
	RbF	20	20 9		5 88		
	UF <sub>4</sub>	27	84 8		12 66		
14 (Flinak)	KF	43 5	25 3	44 9	10 19	17 36	2 59
	LiF	44 5	11 5		5 01		
	NaF	10 9	4 6		1 64		
	UF <sub>4</sub>	1 1	3 5		52		
15	NaF	29 5	12 4	50 3	4 44	21 53	2 34
	BeF <sub>2</sub>	64 0	30 1		15 19		
	KF	4 9	2 8		1 15		
	UF <sub>4</sub>	1 6	5 0		75		
16	NaF	34 0	14 3	68 0	5 12	22 76	2 99
	BeF <sub>2</sub>	57 5	27 0		13 65		
	UF <sub>4</sub>	8 5	26 7		3 99		

<sup>7</sup>Taken from Lange's Handbook of Chemistry,  
Eighth Edition



TABLE 3 (Con't )

CALCULATION OF ROOM TEMPERATURE  
DENSITIES OF FLUORIDE MIXTURES

Mixture	Component	$f_i$	$M_i f_i$	Mol Wt of Mixture	$(M_i/\rho_i)f_i$	Mol Vol of Mixture	$\rho_{\text{Room Temp}}$
17	NaF	47 0	19 7	50 0	7 07	20 12	2 49
	BeF <sub>2</sub>	51 0	24 0		12 11		
	UF <sub>4</sub>	2 0	6 3		94		
18	NaF	45 0	18 9	96 5	6 77	20 80	4 64
	LiF	33 0	8 5		3 72		
	UF <sub>4</sub>	22 0	69 1		10 31		
19	NaF	5 0	2 1	108 2	75	29 49	3 67
	KF	51 0	29 6		11 95		
	ZrF <sub>4</sub>	42 0	70 2		15 85		
	UF <sub>4</sub>	2 0	6 3		94		
20	NaF	5 0	2 1	104 2	75	29 16	3 57
	KF	52 0	30 2		12 18		
	ZrF <sub>4</sub>	43 0	71 9		16 23		
21	NaF	4 8	2 0	112 1	72	29 83	3 76
	KF	50 1	29 1		11 74		
	ZrF <sub>4</sub>	41 3	69 1		15 59		
	UF <sub>4</sub>	3 8	11 9		1 78		
22	KF	46 0	26 7	122 9	10 78	31 53	3 90
	ZrF <sub>4</sub>	50 0	83 6		18 87		
	UF <sub>4</sub>	4 0	12 6		1 88		
23	KF	41 8	24 3	42 9	9 79	16 99	2 53
	NaF	11 4	4 8		1 72		
	LiF	46 2	12 0		5 20		
	ThF <sub>4</sub>	0 6	1 8		28		
24	KF	18 0	10 5	102 5	4 22	27 00	3 80
	NaF	36 0	15 1		5 42		
	ZrF <sub>4</sub>	46 0	76 9		17 36		

TABLE 3 (Con't )

CALCULATION OF ROOM TEMPERATURE  
DENSITIES OF FLUORIDE MIXTURES

Mixture	Component	$f_1$	$M_1 f_1$	Mol Wt of Mixture	$(M_1/\rho_1)f_1$	Mol Vol of Mixture	$\rho_{\text{Room Temp}}$
25	KF	17 4	10 1	109 9	4 08	27 70	3 97
	NaF	34 7	14 6		5 22		
	ZrF <sub>4</sub>	44 4	74 2		16 76		
	UF <sub>4</sub>	3 5	11 0		1 64		
25a	NaF	35 1	14 7	107 7	5 28	27 48	3 92
	KF	17 6	10 2		4 12		
	ZrF <sub>4</sub>	44 8	74 9		16 91		
	UF <sub>4</sub>	2 5	7 9		1 17		
26	KF	14 0	8 1	111 6	3 28	27 78	4 02
	NaF	36 6	15 4		5 51		
	ZrF <sub>4</sub>	45 6	76 2		17 21		
	UF <sub>4</sub>	3 8	11 9		1 78		
27	NaF	46 0	19 3	115 5	6 92	27 67	4 17
	ZrF <sub>4</sub>	50 0	83 6		18 87		
	UF <sub>4</sub>	4 0	12 6		1 88		
28	NaF	48 0	20 2	107 1	7 22	26 84	3 99
	ZrF <sub>4</sub>	52 0	86 9		19 62		
29	NaF	42 2	17 7	114 3	6 35	28 16	4 06
	ZrF <sub>4</sub>	57 8	96 6		21 81		
30	NaF	50 0	21 0	110 5	7 53	26 77	4 13
	ZrF <sub>4</sub>	46 0	76 9		17 36		
	UF <sub>4</sub>	4 0	12 6		1 88		
31	NaF	50 0	21 0	104 6	7 53	26 40	3 96
	ZrF <sub>4</sub>	50 0	83 6		18 87		
32	NaF	52 0	21 8	102 1	7 83	25 95	3 93
	ZrF <sub>4</sub>	48 0	80 3		18 12		

TABLE 3 (Con't )

CALCULATION OF ROOM TEMPERATURE  
DENSITIES OF FLUORIDE MIXTURES

Mixture	Component	$f_1$	$M_1 f_1$	Mol Wt of Mixture	$(M_1/\rho_1)f_1$	Mol Vol of Mixture	$\rho_{\text{Room Temp}}$
33	NaF	50 0	21 0	141 4	7 53	28 69	4 93
	ZrF <sub>4</sub>	25 0	41 8		9 44		
	UF <sub>4</sub>	25 0	78 6		11 72		
34	NaF	57 0	23 9	95 8	8 58	24 81	3 86
	ZrF <sub>4</sub>	43 0	71 9		16 23		
35	NaF	57 0	23 9	44 1	8 59	18 80	2 35
	BeF <sub>2</sub>	43 0	20 2		10 21		
36	NaF	55 0	23 1	57 6	8 28	20 12	2 86
	BeF <sub>2</sub>	40 0	18 8		9 50		
	UF <sub>4</sub>	5 0	15 7		2 34		
37	NaF	50 0	21 0	178 05	7 53	30 97	5 75
	UF <sub>4</sub>	50 0	157 05		23 44		
38	NaF	50 0	21 0	107 54	7 53	26 59	4 04
	ZrF <sub>4</sub>	48 0	80 26		18 12		
	UF <sub>4</sub>	2 0	6 28		94		
39	NaF	65 0	27 3	115 18	9 78	24 82	4 64
	ZrF <sub>4</sub>	15 0	25 08		5 66		
	UF <sub>4</sub>	20 0	62 80		9 38		
40	NaF	53 0	22 3	106 8	7 98	26 09	4 09
	ZrF <sub>4</sub>	43 0	71 9		16 23		
	UF <sub>4</sub>	4 0	12 6		1 88		
41	NaF	63 0	26 46	105 95	9 48	24 55	4 32
	ZrF <sub>4</sub>	25 0	41 8		9 44		
	UF <sub>4</sub>	12 0	37 69		5 63		

TABLE 3 (Con't )  
CALCULATION OF ROOM TEMPERATURE  
DENSITIES OF FLUORIDE MIXTURES

Mixture	Component	$f_1$	$M_1 f_1$	Mol Wt of Mixture	$(M_1/\rho_1)f_1$	Mol Vol of Mixture	$\rho_{\text{Room Temp}}$
42	NaF	64 5	27 09	129 78	9 71	25 80	5 03
	ZrF <sub>4</sub>	6 0	10 03		2 26		
	UF <sub>4</sub>	29 5	92 66		13 83		
43	NaF	66 7	28 0	132 6	10 04	25 67	5 17
	UF <sub>4</sub>	33 3	104 6		15 63		
44	NaF	53 5	22 5	109 8	8 05	26 20	4 19
	ZrF <sub>4</sub>	40 0	66 9		15 10		
	UF <sub>4</sub>	6 5	20 4		3 05		
45	NaF	53 0	22 27	100 87	7 98	25 72	3 92
	ZrF <sub>4</sub>	47 0	78 6		17 74		
46	NaF	62 5	26 3	125 7	9 41	25 85	4 86
	ZrF <sub>4</sub>	12 5	20 9		4 72		
	UF <sub>4</sub>	25 0	78 5		11 72		
47	NaF	35	14 7	41 1	5 27	18 20	2 26
	LiF	20	5 2		2 25		
	BeF <sub>2</sub>	45	21 2		10 68		
C Test	NaF	66 7	28 0	83 7	10 04	22 61	3 70
	ZrF <sub>4</sub>	33 3	55 7		12 57		
50-99	(to be hydroxide mixtures)						
100	LiF	60 0	15 5	32 3	6 76	12 78	2 53
	NaF	40 0	16 8		6 02		
101	LiF	57 6	14 9	43 6	6 49	14 15	3 08
	NaF	38 4	16 1		5 78		
	UF <sub>4</sub>	4 0	12 6		1 88		

TABLE 3 (Con't )

CALCULATION OF ROOM TEMPERATURE  
DENSITIES OF FLUORIDE MIXTURES

Mixture	Component	$f_1$	$M_1 f_1$	Mol Wt of Mixture	$(M_1/\rho_1)f_1$	Mol Vol of Mixture	$\rho_{\text{Room Temp}}$
102	LiF	50 0	13 0	42 1	5 63	17 35	2 43
	KF	50 0	29 1		11 72		
103	LiF	48 0	12 4	52 9	5 41	18 54	2 85
	KF	48 0	27 9		11 25		
	UF <sub>4</sub>	4 0	12 6		1 88		
104	RbF	57 0	59 6	70 7	16 75	21 59	3 27
	LiF	43 0	11 1		4 84		
105	RbF	54 7	57 2	80 5	16 07	22 60	3 56
	LiF	41 3	10 7		4 65		
	UF <sub>4</sub>	4	12 6		1 88		

107 -----  $\approx 2.09 @ 800^\circ\text{C}$

/ for  $C_p$  see ORNL-1956

Th Cond. of 107 -  $1.035 \frac{\text{W}}{\text{cm}^\circ\text{C}}$

2 BTU

For Inf.  
Cohen,  
Powers

TABLE 4

CALCULATED DENSITY-TEMPERATURE RELATIONSHIPS  
FOR ALL FLUORIDE MIXTURES  
COMPARISON OF CALCULATED RELATIONSHIPS AND  
AVAILABLE EXPERIMENTAL RELATIONSHIPS

Composition	M P (°C)	Calculated Density	Experimental Density	Agreement <sup>8</sup>	Reference
1	480	$\rho = 3 \ 60 - 0 \ 00087T$			
2	530	$\rho = 4 \ 55 - 0 \ 00102T$	$\rho = 4 \ 70 - 0 \ 00115T$	$> 2\%$	2,12
2a	558	$\rho = 4 \ 40 - 0 \ 00099T$	$\rho = 4 \ 54 - 0 \ 00110T$	$> 2\%$	3,12
3	465	$\rho = 3 \ 24 - 0 \ 00082T$			
4	708	$\rho = 5 \ 60 - 0 \ 00116T$			
5	465	$\rho = 6 \ 01 - 0 \ 00122T$			
6	435	$\rho = 2 \ 29 - 0 \ 00065T$			
7	575	$\rho = 4 \ 78 - 0 \ 00104T$			
8	992 <sup>7</sup>				
9	800 <sup>7</sup>				
10	870 <sup>7</sup>				
11	880 <sup>7</sup>				
12	460	$\rho = 2 \ 47 - 0 \ 00068T$	$\rho = 2 \ 53 - 0 \ 00073T$	$> 2\%$	11
13	490	$\rho = 5 \ 05 - 0 \ 00108T$			
14	452	$\rho = 2 \ 56 - 0 \ 00070T$	$\rho = 2 \ 65 - 0 \ 00090T$	$> 3\%$	4,12
15	433	$\rho = 2 \ 40 - 0 \ 00067T$			
16	500	$\rho = 2 \ 87 - 0 \ 00075T$			
17		$\rho = 2 \ 49 - 0 \ 00069T$			
18	506	$\rho = 4 \ 54 - 0 \ 00101T$			
19	405	$\rho = 3 \ 46 - 0 \ 00085T$	$\rho = 3 \ 78 - 0 \ 00109T$	6% (600°C)	5,12
20	450	$\rho = 3 \ 38 - 0 \ 00084T$			
21	540	$\rho = 3 \ 55 - 0 \ 00087T$	$\rho = 4 \ 27 - 0 \ 00163T$	$> 4\%$ (800°C)	5,12
22	605	$\rho = 3 \ 69 - 0 \ 00089T$			
23	450	$\rho = 2 \ 52 - 0 \ 00070T$			
24	450	$\rho = 3 \ 59 - 0 \ 00087T$			
25	545	$\rho = 3 \ 75 - 0 \ 00090T$	$\rho = 3 \ 78 - 0 \ 00091T$	$> 1\%$	5,12
25a	545	$\rho = 3 \ 71 - 0 \ 00089T$	$\rho = 3 \ 65 - 0 \ 00080T$	$> 1\%$	5,12
26	540	$\rho = 3 \ 82 - 0 \ 00091T$			
27	510	$\rho = 4 \ 97 - 0 \ 00093T$			

TABLE 4 (Con't )

CALCULATED DENSITY-TEMPERATURE RELATIONSHIPS  
FOR ALL FLUORIDE MIXTURES  
COMPARISON OF CALCULATED RELATIONSHIPS AND  
AVAILABLE EXPERIMENTAL RELATIONSHIPS

Composition	M P (°C)	Calculated Density	Experimental Density	Agreement <sup>8</sup>	Reference
28	510	$\rho = 3.79 - 0.00090T$			
29	570	$\rho = 3.86 - 0.00092T$			
30	520	$\rho = 3.93 - 0.00093T$			
31	510	$\rho = 3.75 - 0.00090T$	$\rho = 3.79 - 0.00093T$	>1%	6,12
32	500	$\rho = 3.72 - 0.00089T$			
33	610	$\rho = 4.90 - 0.00107T$	$\rho = 5.09 - 0.00159T$	>5%	6,12
34	490	$\rho = 3.65 - 0.00088T$			
35	360	$\rho = 2.40 - 0.00067T$			
36	>500	$\rho = 2.76 - 0.00073T$			
37	715	$\rho = 6.16 - 0.00123T$			
38	510	$\rho = 3.83 - 0.00091T$			
39	610	$\rho = 4.55 - 0.00102T$			
40	520	$\rho = 3.89 - 0.00092T$	$\rho = 3.60 - 0.00055T$	>2%	7
41	595	$\rho = 4.15 - 0.00096T$			
42	650	$\rho = 5.05 - 0.00107T$			
43	640	$\rho = 5.25 - 0.00111T$	$\rho = 5.51 - 0.00130T$	>3%	8
44	545	$\rho = 4.00 - 0.00093T$	$\rho = 4.04 - 0.00110T$	>3%	9
45	500	$\rho = 3.71 - 0.00089T$			
46	635	$\rho = 4.83 - 0.00105T$	$\rho = 4.75 - 0.00120T$	>5%	10
47	350 ± 20°	$\rho = 2.33 - 0.00066T$			
C Test	625	$\rho = 3.49 - 0.00086T$			
100	652	$\rho = 2.52 - 0.00069T$	$\rho = 2.42 - 0.00055T$	>1%	11
101	645	$\rho = 2.95 - 0.00077T$			
102	492	$\rho = 2.46 - 0.00068T$			
103	>500	$\rho = 2.75 - 0.00073T$			
104	462	$\rho = 3.10 - 0.00079T$			
105	465?	$\rho = 3.36 - 0.00084T$			

<sup>8</sup> Agreement or percent difference =  $\frac{\rho_{\text{exp}} - \rho_{\text{calc}}}{1/2 (\rho_{\text{exp}} + \rho_{\text{calc}})} \times 100$   
(Determined at 700°C unless otherwise stated)